

GGB DP4™ and DP4-B™

Metal-Polymer Self-lubricating Lead Free Bearing Solutions



The Global Leader
in High Performance Bearing Solutions



an EnPro Industries company

Quality

All the products described in this handbook are manufactured under DIN EN ISO 9001, ISO/TS 16949 and ISO 14001 approved quality management systems.

All Certificates can be downloaded as PDF files from our website www.ggbearings.com.

In addition GGB North America has been certified AS9100 revision B complying with the requirements of aerospace industry's quality management system for the manufacture of metal-backed bearings and filament wound bearings and washers.

AMERICA



FRANCE



GERMANY



BRAZIL



SLOVAKIA



CHINA



Content

Quality	1	5 Lubrication	23
1 Introduction	5	5.1 Lubricants	23
1.1 Characteristics and Advantages	5	5.2 Tribology	23
1.2 Applications	6	Hydrodynamic lubrication	23
2 Structure and Composition	7	Mixed film lubrication	24
2.1 Basic Forms	7	Boundary lubrication	24
Standard Components	7	5.3 Characteristics of Lubricated Bearings	24
Non-Standard Components	7	5.4 Design Guidance	25
3 Properties	8	5.5 Clearances for lubricated operation	26
3.1 Physical and Mechanical Properties	8	5.6 Grooving for lubricated operation	26
3.2 Chemical Properties	8	5.7 Mating Surface Finish for lubricated operation	26
3.3 Frictional Properties	9	5.8 Grease Lubrication	26
Effect of Temperature for unlubricated applications	9	6 Bearing Assembly	27
4 Bearing Performance ..	10	Dimensions and Tolerances	27
4.1 McPherson Strut Applications ..	10	6.1 Allowance for Thermal Expansion	27
Wear and Friction Properties ...	10	6.2 Tolerances for minimum clearance	28
McPherson Strut Test Rig	10	Burnishing	28
Cavitation Erosion Resistance ..	12	6.3 Counterface Design	29
Flow Erosion Resistance	13	6.4 Installation	30
4.2 Hydraulic Applications	14	Fitting of cylindrical Bushes	30
GGB Jupiter Test Rig	14	Fitting of flanged bushes	30
4.3 Dry Wear Performance	15	Insertion Forces	30
Design Factors	15	Alignment	31
Oscillating Movement	16	Sealing	31
Application Factors	17	6.5 Axial Location	31
Mating Surface	18	Fitting of Thrust Washers	31
Bore Burnishing	19	Slideways	32
Type of Load	19	7 Modification	33
4.4 Calculation of Bearing Service Life	20	7.1 Cutting and Machining	33
Specific load p	20	Drilling Oil Holes	33
High load factor a_E	20	Cutting Strip Material	33
Modified pv Factor	20	7.2 Electroplating	33
Estimation of bearing life L_H	20	DP4 Components	33
Bore Burnishing	21		
Slideways	21		
4.5 Worked Examples	22		

8	Standard Products	34	9	Test Methods	49
8.1	DP4 Cylindrical bushes	34	9.1	Measurement of Wrapped Bushes	49
8.2	DP4 Flanged bushes	40		Test A of ISO 3547 Part 2	49
8.3	DP4 Flanged Washers	42		Test B (alternatively to Test A)	49
8.4	DP4 Thrust Washers	43		Test C	49
8.5	DP4B Cylindrical bushes	44		Measurement of Wall Thickness (alternatively to Test C)	49
8.6	DP4B Flanged bushes	46		Test D	49
8.7	DP4 Strip	48	10	Data Sheet for bearing design	50
8.8	DP4B Strip	48		Formula Symbols and Designations	51

1 Introduction

The purpose of this handbook is to provide comprehensive technical information on the characteristics of DP4™ and DP4B™ bearings.

The information given permits designers to establish the correct size of bearing required and the expected life and performance.

In addition, your local sales representative is available to assist you with your design.

Complete information on the range of DP4 standard stock products is given together with details of other DP4 products.

GGB is continually refining and extending its experimental and theoretical knowledge and, therefore, when using this brochure it is always worth-while to contact GGB should additional information be required.

As it is impossible to cover all conditions of operation which arise in practice, customers are advised to carry out prototype testing wherever possible.

1.1 Characteristics and Advantages

The DP4 and DP4B materials offer the following characteristics:

- Good frictional properties with negligible stick-slip
- High static and dynamic load capacity
- Suitable for rotating, oscillating, reciprocating and sliding movements
- Compact size and low weight
- Prefinished that requires no machining after assembly
- Possibility to burnish for reduced operating clearance
- No water absorption and therefore dimensionally stable
- Suitable for a wide operating temperature range from -200 to +280 °C
- DP4B with bronze backing for increased corrosion resistance
- **Lead free in compliance with European RoHS 2002/95/EC, 2002/96/EC and EVL 2000/53/EC directives (see page 51)**

In particular, depending on the dry running conditions, DP4 and DP4B materials

Dry conditions

- Good friction and wear performance under light duty conditions
- Particularly suitable for intermittent oscillating and reciprocating movements
- Maintenance free as no external lubrication required
- Seizure resistant.

present the following performance advantages:

Lubricated conditions

- Good wear and friction performance over a wide range of load, speed and temperature conditions
- High wear resistance in boundary operating conditions
- High resistance of bearing surface under fluid cavitation and flow erosion conditions
- Suitable for operation in diverse fluids (oil, fuel, solvents, refrigerants, water).

1.2 Applications

Given the performance characteristics in both dry and lubricated operating conditions, DP4 and DP4B bearing

Automotive

Braking systems, clutches, gearbox and transmissions, hinges - door bonnet and boot, convertible roof tops, pedal systems, pumps - axial, radial, gear and vane, seat mechanisms, steering systems, struts and shock absorbers, wiper systems.

materials are extensively used in a wide range of automotive and industrial applications, such as:

Industrial

Aerospace, agricultural, construction equipment, food and beverage, marine, material handling, office equipment, packaging equipment, pneumatic and hydraulic cylinders, railroad and tramways, textile machinery, valves.



Fig. 1: Applications for DP4 and DP4B

2 Structure and Composition

DP4 is a composite bearing material. It consists of a steel DP4/bronze DP4B backing to which is bonded a porous sinter bronze interlayer which is overlaid and impregnated with Polytetrafluoroethylene (PTFE) containing a mixture of inorganic

fillers and special polymer fibres. The steel DP4/bronze DP4B backing provides mechanical strength and the bronze sinter layer provides a strong mechanical bond for the filled bearing lining.

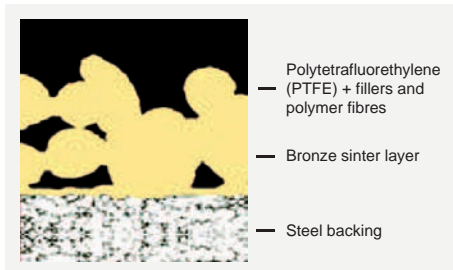


Fig. 2: DP4-microsection

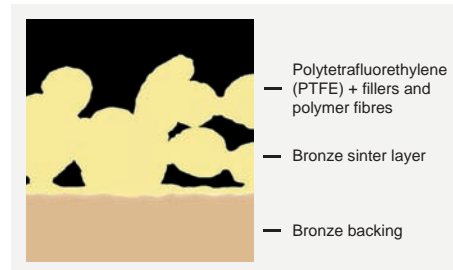


Fig. 3: DP4B-microsection

2.1 Basic Forms

Standard Components

These products are manufactured to International, National or GGB standards. The following components are standard stock products:

- Cylindrical Bushes
- Flanged Bushes
- Thrust Washers
- Flanged Washers
- Strip Material

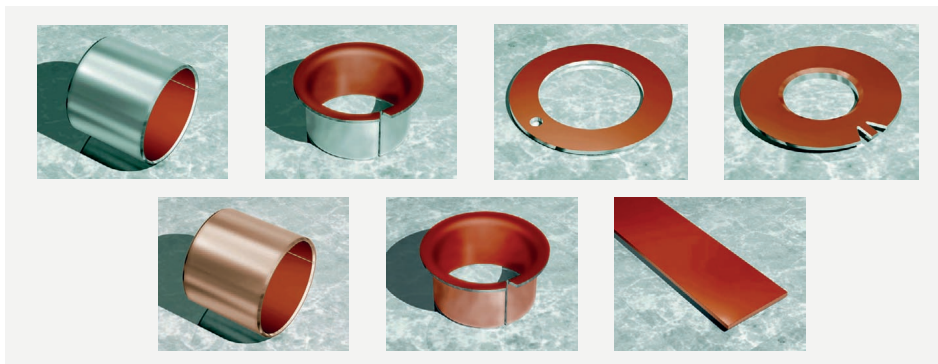


Fig. 4: Standard stock products

Non-Standard Components

These products are manufactured to customer's requirements and include for example:

- Modified Standard Components
- Half Bearings
- Flat Components
- Deep Drawn Parts
- Pressings
- Stampings

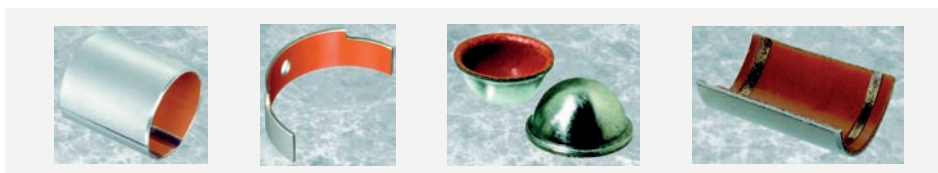


Fig. 5: Non-Standard Components

3 Properties

3.1 Physical and Mechanical Properties

	Symbol	Value		Unit	Comment	
		DP4	DP4B			
Physical Properties	Coefficient of linear thermal expansion:					
	Parallel to surface	α_1	11	18	$10^{-6}/K$	
	Normal to surface	α_2	30	36	$10^{-6}/K$	
	Maximum Operating Temperature	T_{max}	+280	+280	°C	
	Minimum Operating Temperature	T_{min}	-200	-200	°C	
Mechanical Properties	Compressive Yield Strength	σ_c	350	300	MPa	measured on disc 5 mm diameter x 2.45 mm thick.
	Maximum Load					
	Static	$P_{sta,max}$	250	140	MPa	
	Dynamic	$P_{dyn,max}$	140	140	MPa	

Table 1: Physical and mechanical properties of DP4 and DP4B

3.2 Chemical Properties

The following table provides an indication of the chemical resistance of DP4 to various chemical media.

It is recommended, that the chemical resistance is confirmed by testing.

+	Satisfactory: Corrosion damage is unlikely to occur.
o	Acceptable: Some corrosion damage may occur but this will not be sufficient to impair either the structural integrity or the tribological performance of the material.
-	Unsatisfactory: Corrosion damage will occur and is likely to affect either the structural integrity and/or the tribological performance of the material.

	Chemical	%	°C	Rating	
				DP4	DP4B
Strong Acids	Hydrochloric Acid	5	20	-	-
	Nitric Acid	5	20	-	-
	Sulphuric Acid	5	20	-	-
Weak Acids	Acetic Acid	5	20	-	o
	Formic Acid	5	20	-	o
Bases	Ammonia	10	20	o	-
	Sodium Hydroxide	5	20	o	o
Solvents	Acetone		20	+	+
	Carbon Tetrachloride		20	+	+
Lubricants and fuels	Paraffin		20	+	+
	Gasolene		20	+	+
	Kerosene		20	+	+
	Diesel Fuel		20	+	+
	Mineral Oil		70	+	+
	HFA-ISO46 High Water Fluid		70	+	+
	HFC-Water-Glycol		70	+	+
	HFD-Phosphate Ester		70	+	+
	Water		20	o	+
	Sea Water		20	-	o

Table 2: Chemical resistance of DP4 and DP4B

3.3 Frictional Properties

DP4 bearings show negligible 'stick-slip' and provide smooth sliding between adjacent surfaces. The coefficient of friction of DP4 depends upon:

- The specific load p [MPa]
- The sliding speed v [m/s]
- The roughness of the mating running surface R_a [μm]
- The bearing temperature T [$^{\circ}\text{C}$].

A typical relationship is shown in Fig. 6, which can be used as a guide to establish

the actual friction under clean, dry conditions after running in.

Exact values may vary by $\pm 20\%$ depending on operating conditions. Before running in, the friction may be up to 50% higher.

After progressively longer periods of dwell under load (e.g. hours or days) the static coefficient of friction on the first movement may be between 1.5 and 3 times greater, particularly before running in.

Effect of Temperature for unlubricated applications

The coefficient of friction of DP4 varies with temperature. Typical values are shown in Fig. 7 for temperatures up to 250 $^{\circ}\text{C}$. Friction increases at bearing temperatures below 0 $^{\circ}\text{C}$.

Where frictional characteristics are critical to a design they should be established by prototype testing.

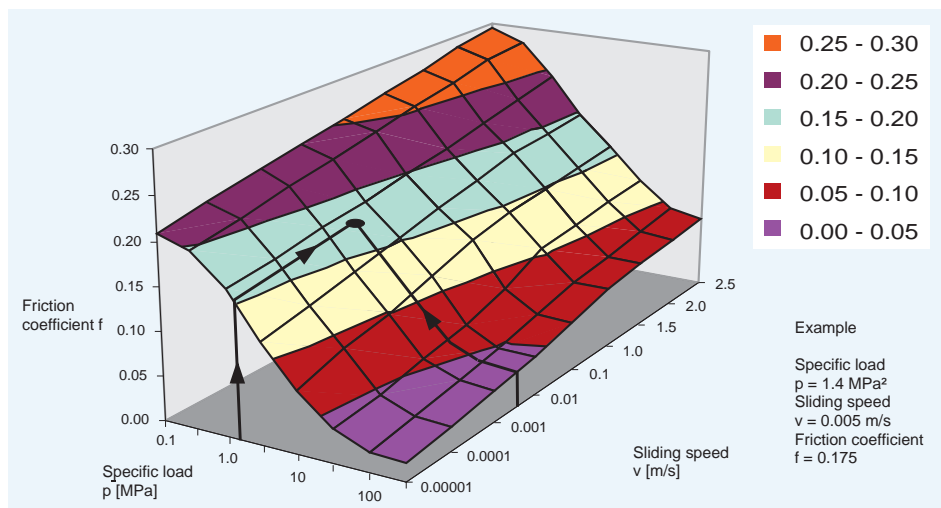


Fig. 6: Variation of friction coefficient f with specific load p and speed v at temperature $T = 25 \text{ }^{\circ}\text{C}$

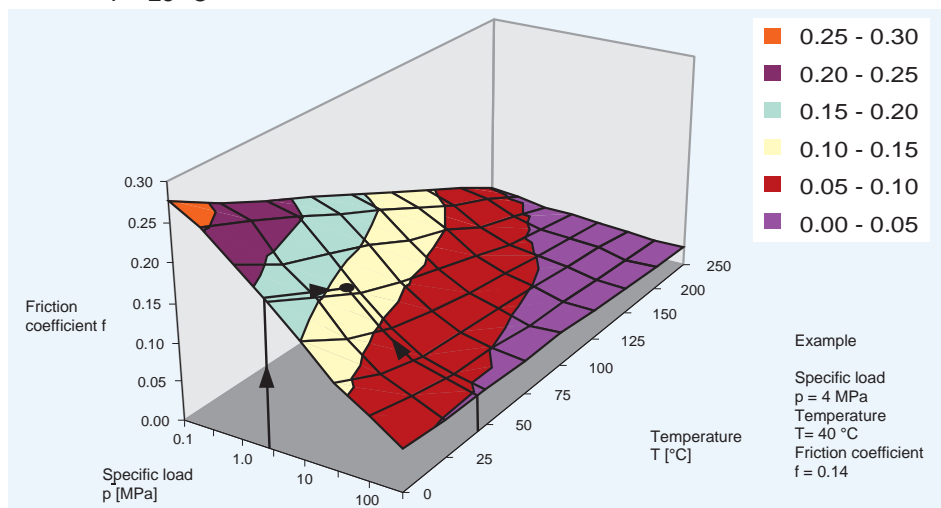


Fig. 7: Variation of friction coefficient f with specific load p and temperature T at speed $v = 0.01 \text{ m/s}$

4 Bearing Performance

4.1 McPherson Strut Applications

DP4 has been developed to provide improved wear, erosion resistance and reduced friction in McPherson strut piston rod guide bush applications under the most demanding of operating conditions.

In the following sections, the performance of DP4 is compared with that of the material used in the majority of this type of application.

Wear and Friction Properties

The wear and frictional performance of DP4 has been evaluated in the piston rod guide bush application of a McPherson strut shock absorber using the test rig shown in Fig. 8. The test conditions are

designed to simulate the operational duty of the test strut in service and differ in detail according to the strut manufacturer. The test conditions used are given in Table 3 and Table 4.

McPherson Strut Test Rig

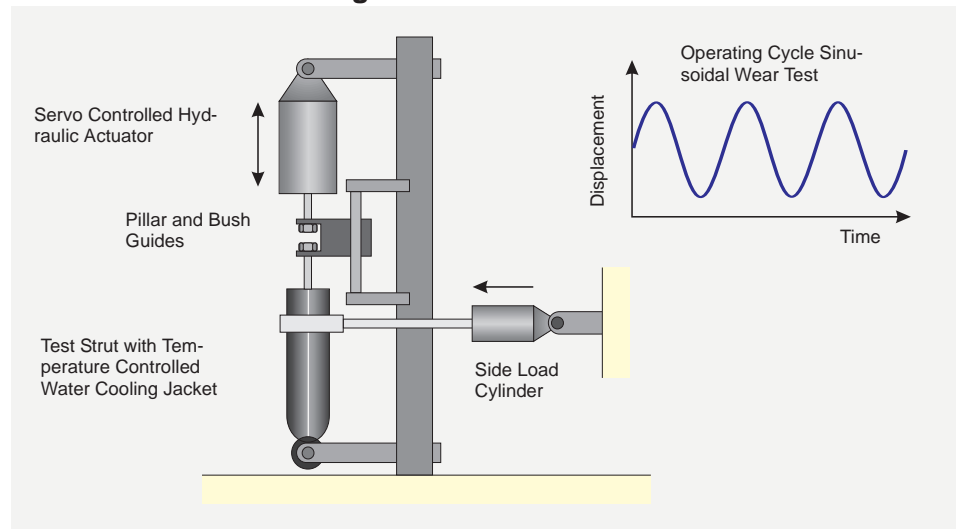


Fig. 8: Principle of the Strut Test Rig

Strut Wear - Test conditions

Waveform	Sine
Frequency	2.5 Hz
Side Load	890 N
Test Duration	100 hours
Stroke	100 mm
Mean Diametral Clearance	0.06 mm
Lubricant	TEX 0358
Foot Valve Temperature	70 °C

Table 3: McPherson strut wear test conditions

Strut Friction - Test conditions

Waveform	Sine
Frequency	0.1 Hz
Side Load	600 N
Stroke	70 mm
Mean Diametral Clearance	0.06 mm
Lubricant	TEX 0358
Foot Valve Temperature	Ambient

Table 4: McPherson strut friction test conditions

The relative wear and frictional performance of DP4 tested under these conditions are shown in Figures 9-11. Actual results for the wear rate and friction are not quoted because these depend

strongly on the actual test conditions and design of the strut under test. The relative performance plots shown thus provide the best indication as to the benefits offered by DP4 in this class of application.

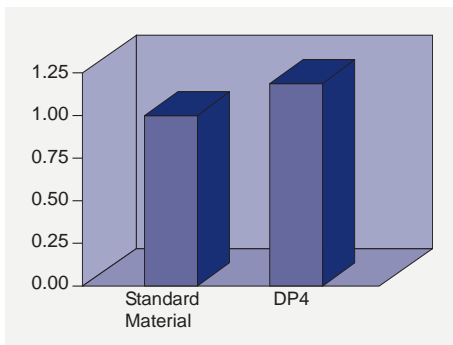


Fig. 9: Relative wear resistance

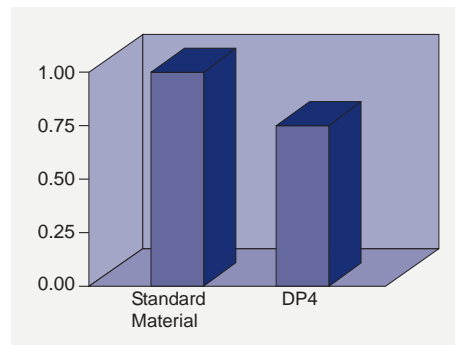


Fig. 10: Relative static friction coefficient

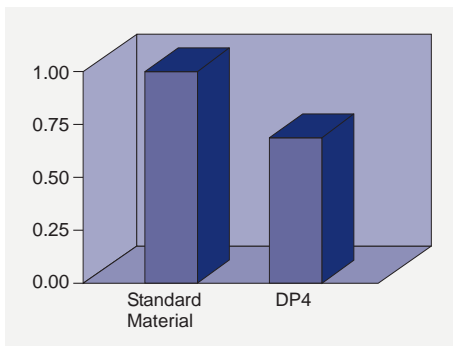


Fig. 11: Relative dynamic friction coefficient

Cavitation Erosion Resistance

Under certain operating conditions, the PTFE lining of the McPherson strut piston rod guide bush can suffer erosion damage, due to cavitation and flow erosion effects from the oil film within the bearing. The test

rig shown in Fig. 12 is designed to reproduce the cavitation erosion damage to the bearing lining of the test specimen. The test conditions are given in Table 5.

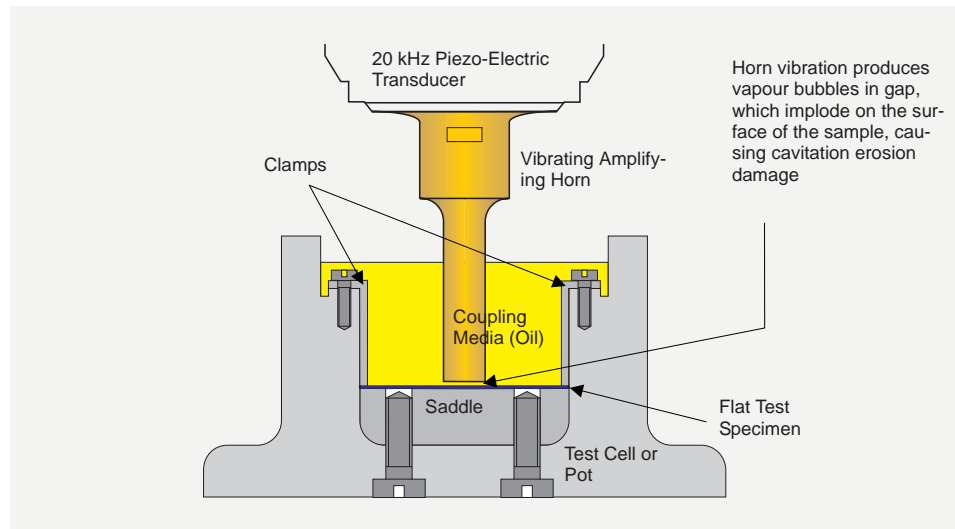


Fig. 12: Principle of the cavitation erosion test rig

Cavitation Erosion - Test Conditions

Amplitude	0.015 mm
Frequency	20 kHz
Separation	1 mm
Test Duration	30 minutes
Lubricant	TEX 0358
Temperature	Ambient

Table 5: Cavitation erosion test conditions

The relative resistance to cavitation damage of DP4 as evaluated on this test rig is shown in Fig. 13.

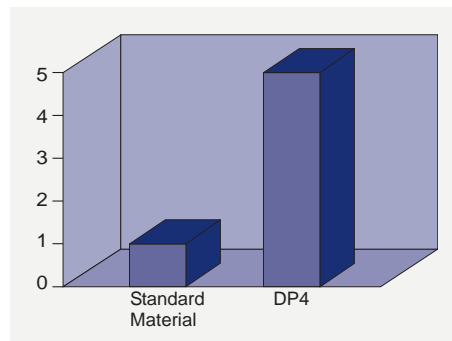


Fig. 13: Relative resistance to cavitation erosion

Flow Erosion Resistance

The test rig shown in Fig. 14 is designed to reproduce flow erosion damage to the bearing lining of the test specimen. The test conditions are given in Table 6.

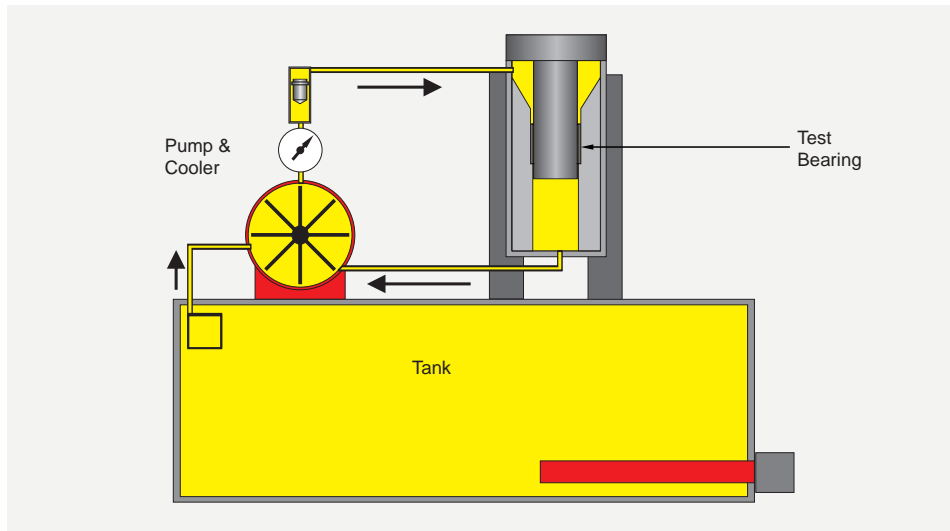


Fig. 14: Principle of the flow erosion test rig

Flow Erosion - Test Conditions

Bearing Diameter	20 mm
Bearing Length	15 mm
Diametral Clearance	0.11 mm
Pressure	13.8 MPa
Flow Rate	5 l/min
Test Duration	20 hours
Shaft Surface Finish	0.15 μm ±0.05
Temperature	Ambient

Table 6: Flow erosion test conditions

The relative resistance to flow erosion damage of DP4 as evaluated on this test rig is shown in Fig. 15.

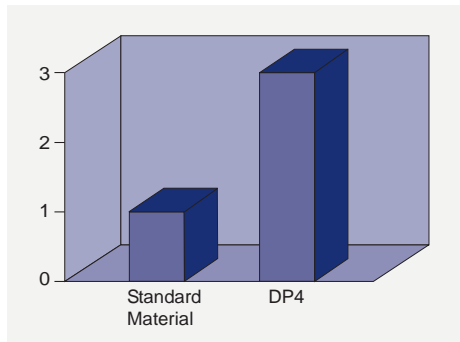


Fig. 15: Relative resistance to flow erosion

4.2 Hydraulic Applications

DP4 also shows excellent wear and frictional performance in a wide range of oil lubricated hydraulic applications.

The wear resistance of DP4 under steady load oil immersed boundary lubrication

conditions has been evaluated using the test rig shown in Fig. 16. The test conditions are given in Table 7.

GGB Jupiter Test Rig

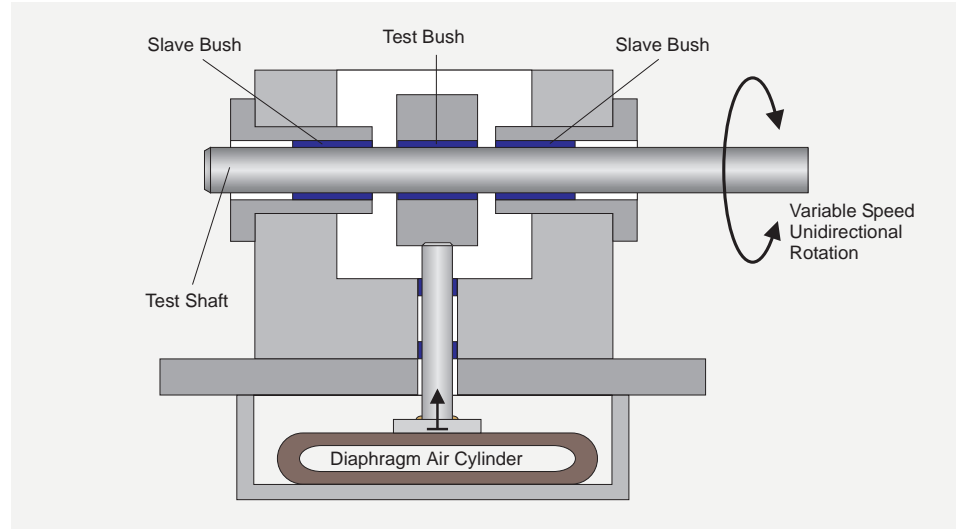


Fig. 16: Principle of the GGB Jupiter test rig

Lubricated Wear - Test Conditions

Bearing Diameter	20 mm
Bearing Length	15 mm
Mean Diametral Clearance	0.10 mm
Speed	0.11 m/s
Lubricant	ISO VG 46 hydraulic oil

Table 7: Lubricated wear test conditions

The relative pv limits with boundary lubrication of DP4 and the material used in many high performance hydraulic pump applications as determined from these

tests are shown in Fig. 17. The limiting pv depends upon the actual operating conditions and hence the relative performance only is given for guidance.

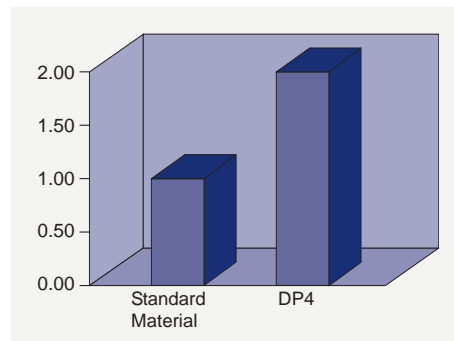


Fig. 17: Relative pv limits

4.3 Dry Wear Performance

Design Factors

The main parameters when determining the size or calculating the service life for a DP4 bearing are:

- Specific Load Limit p_{lim}
- pv Factor
- Mating surface roughness R_a

- Mating surface material
- Temperature T
- Other environmental factors e.g. housing design, dirt, lubrication

The following calculation can be used to estimate the bearing service life of DP4 under dry running conditions.

Specific Load p

For the purpose of assessing bearing performance the specific load p is defined as the working load divided by the projected area of the bearing and is expressed in MPa.

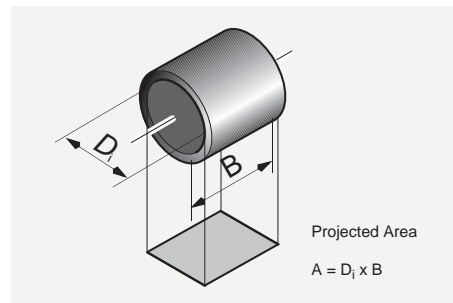


Fig. 18: Projected Area

Cylindrical Bush

(4.3.1) [MPa]

$$p = \frac{F}{D_i \cdot B}$$

Flanged Bush (Axial Loading)

(4.3.3) [MPa]

$$p = \frac{F}{0.04 \cdot (D_{ii}^2 - D_i^2)}$$

Thrust Washer

(4.3.2) [MPa]

$$p = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)}$$

Slideway

(4.3.4) [MPa]

$$p = \frac{F}{L \cdot W}$$

Specific Load Limit p_{lim}

The maximum load which can be applied to a DP4 bearing can be expressed in terms of the Specific Load Limit, which depends on the type of the loading. It is highest under steady loads. Conditions of dynamic load or oscillating movement which produce fatigue stress in the bearing result in a reduction in the permissible Specific Load Limit.

In general the specific load on a DP4 bearing should not exceed the Specific Load Limits given in Table 8.

The values of Specific Load Limit specified in Table 8 assume good alignment between the bearing and mating surface (Fig. 35).

Maximum specific load p_{lim}

Type of loading	p_{lim} [MPa]									
steady load, rotating movement	140									
steady load, oscillating movement										
p_{lim}	140	140	115	95	85	80	60	44	30	20
No. of movement cycles Q	1000	2000	4000	6000	8000	10^4	10^5	10^6	10^7	10^8
dynamic load, rotating or oscillating movement										
p_{lim}	60	60	50	46	42	40	30	22	15	10
No. of load cycles Q	1000	2000	4000	6000	8000	10^4	10^5	10^6	10^7	10^8

Table 8: Specific load limit

Permanent deformation of the DP4 bearing lining may occur for specific loads above 140 MPa unless with slow intermittent movements. Under these conditions, it is recommended to contact GGB for further information.

The permissible maximum load on a thrust washer is higher than that on the flange of a flanged bush, and under conditions of high axial loads a thrust washer should be specified.

Sliding Speed v

Speeds in excess of 2.5 m/s sometimes lead to overheating, and a running in procedure may be beneficial.

This could consist of a series of short runs progressively increasing in duration from an initial run of a few seconds.

Calculation of Sliding Speed v

Continuous Rotation

Cylindrical Bush

$$(4.3.5) \quad v = \frac{D_i \cdot \pi \cdot n}{60 \cdot 10^3} \quad [\text{m/s}]$$

Thrust Washer

$$(4.3.6) \quad v = \frac{D_o + D_i}{2} \cdot \pi \cdot n \quad [\text{m/s}]$$

Oscillating Movement

Cylindrical Bush

$$(4.3.7) \quad v = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\varphi \cdot n_{osc}}{360} \quad [\text{m/s}]$$

Thrust Washer

$$(4.3.8) \quad v = \frac{D_o + D_i}{2} \cdot \pi \cdot \frac{4\varphi \cdot n_{osc}}{360} \quad [\text{m/s}]$$

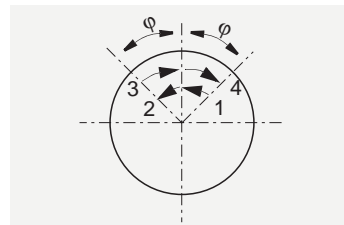


Fig. 19: Oscillating movement

pv Factor

The useful operating life of a DP4 bearing is governed by the pv factor, the product of the specific load p [MPa] and the sliding speed v [m/s].

For thrust washers and flanged bush thrust faces the rubbing velocity at the mean diameter is used.

	DP4	Unit
p	140	MPa
v	2.5	m/s
pv continuous	0.5	MPa x m/s
pv intermittent	1.0	MPa x m/s

Table 9: Typical data p, v, pv

pv factors up to 1.0 Mpa x m/s can be accommodated for short periods, whilst for continuous rating, pv factors up to 0.5 MPa x m/s can be used, depending upon the operating life required.

Calculation of pv Factor

$$(4.3.9) \quad pv = p \cdot v \quad [\text{MPa} \times \text{m/s}]$$

Application Factors

The following factors influence the bearing performance of DP4 and must be considered in calculating the required

dimensions or estimating the bearing life for a particular application.

Temperature

The useful life of a DP4 bearing depends upon the operating temperature.

properties of the housing and the mating surface. Intermittent operation affects the heat dissipation from the assembly and hence the operating temperature of the bearing.

Under dry running conditions frictional heat is generated at the rubbing surface of the bearing dependent on the pv condition. For a given pv factor the operating temperature of the bearing depends upon the temperature of the surrounding environment, the heat dissipation

The effect of temperature on the operating life of DP4 bearings is indicated by the factor a_T shown in Table 10.

Mode of Operation	Nature of housing	Temperature of bearing environment T_{amb} [°C] and Temperature application factor a_T					
		25	60	100	150	200	280
Dry continuous operation	Average heat dissipating qualities	1.0	0.8	0.6	0.4	0.2	0.1
Dry continuous operation	Light pressings or isolated housing with poor heat dissipating qualities	0.5	0.4	0.3	0.2	0.1	-
Dry continuous operation	Non-metallic housings with bad heat dissipating qualities	0.3	0.3	0.2	0.1	-	-
Dry intermittent operation (duration less than 2 min, followed by a longer dwell period)	Average heat dissipating qualities	2.0	1.6	1.2	0.8	0.4	0.2

Table 10: Temperature application factor a_T

Mating Surface

The effect of mating surface material type on the operating life of DP4 bearings is indicated by the mating surface factor a_M and life correction constant a_L shown in Table 11.

Note:

The factor values given assume a mating surface finish of $R_a = 0.4 \pm 0.1 \mu\text{m}$.

- A ground surface is preferred to fine turned.
- Surfaces should be cleaned of abrasive particles after polishing.
- Cast iron surfaces should be ground to $R_a = 0.3 \pm 0.1 \mu\text{m}$.
- The grinding cut should be in the same direction as the bearing motion relative to the shaft.

Material	Mating Surface Factor a_M	Life correction constant a_L
Steel and Cast Iron		
Carbon Steel	1	400
Carbon Manganese Steel	1	400
Alloy Steel	1	400
Case Hardened Steel	1	400
Nitrided Steel	1	400
Salt bath nitrocarburised	1	400
Stainless Steel (7-10 % Ni, 17-20 % Cr)	2	400
Cast Iron ($0.3 \pm 0.1 \mu\text{m } R_a$)	1	400

Table 11: Mating surface factor a_M and life correction constant a_L

Bearing Size

The running clearance of a DP4 bearing increases with bearing diameter resulting in a proportionally smaller contact area between the shaft and bearing. This reduction in contact area has the effect of

increasing the actual unit load and hence p_v factor. The bearing size factor (Fig. 21) is used in the design calculations to allow for this effect.

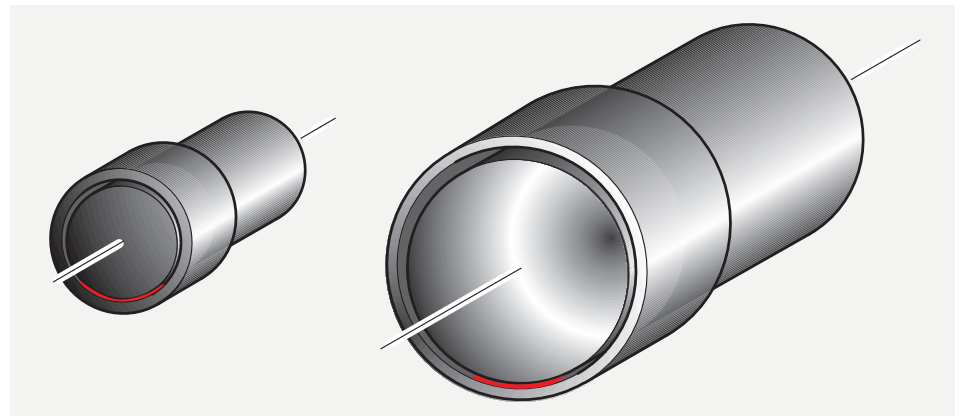


Fig. 20: Contact area between bearing and shaft

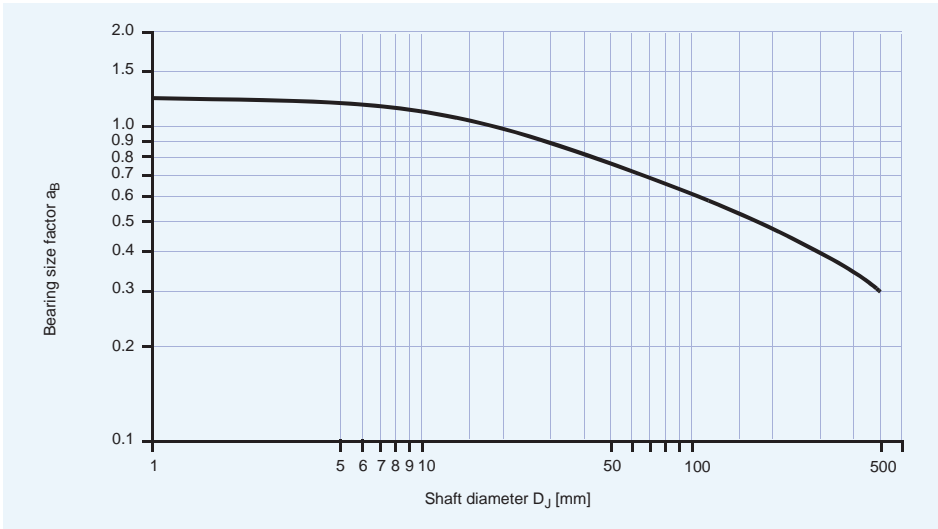


Fig. 21: Bearing size factor a_B

Bore Burnishing

Burnishing the bore of a DP4 bearing results in a reduction in the wear performance. The application factor a_C

given in Table 12 is used in the design calculation to allow for this effect. Machining DP4 is not recommended.

Degree of sizing	Application factor a_C	
Burnishing: Excess of burnishing tool diameter over mean bore size	0.025 mm	0.8
	0.038 mm	0.6
	0.050 mm	0.3

Table 12: Bore burnishing application factor a_C

Type of Load

The type of load is considered in formula (4.4.9), Page 20 and (4.4.10), Page 20.

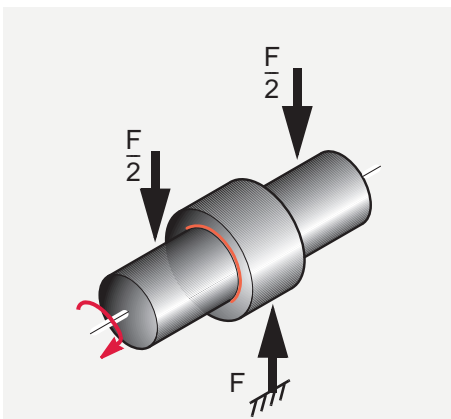


Fig. 22: Steady load, bush stationary, shaft rotating

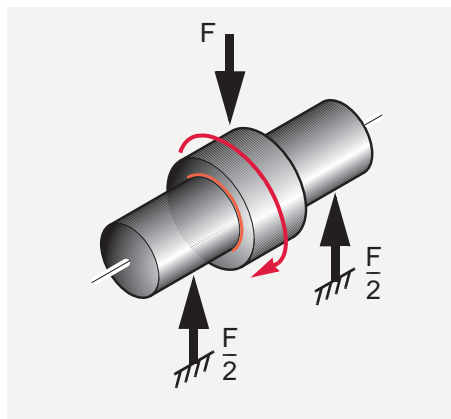


Fig. 23: Rotating load, shaft stationary, bush rotating

4.4 Calculation of Bearing Service Life

Where the size of a bearing is governed largely by the space available the following calculation can be used to determine

whether its useful life will satisfy the requirements. If the calculated life is inadequate, a redesign should be considered.

Specific load p

Bushes

$$(4.4.1) \quad p = \frac{F}{D_i \cdot B} \quad [\text{MPa}]$$

Flanged Bushes

$$(4.4.2) \quad p = \frac{F}{0.04 \cdot (D_{fl}^2 - D_i^2)} \quad [\text{MPa}]$$

Thrust Washers

$$(4.4.3) \quad p = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)} \quad [\text{MPa}]$$

High load factor a_E

If a_E is negative then the bearing is overloaded. Increase the bearing diameter and/or length.

$$(4.4.4) \quad a_E = \frac{p_{lim} - p}{p_{lim}} \quad [-]$$

p_{lim} see Tab. 8, page 14

Modified pv Factor

Bushes

$$(4.4.5) \quad pv = \frac{5.25 \cdot 10^{-5} F \cdot n}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} \quad [\text{MPa} \times \text{m/s}]$$

Flanged Bushes

$$(4.4.6) \quad pv = \frac{6.5 \cdot 10^{-4} F \cdot n}{a_E \cdot (D_{fl} - D_i) \cdot a_T \cdot a_M \cdot a_B} \quad [\text{MPa} \times \text{m/s}]$$

Thrust Washers

$$(4.4.7) \quad pv = \frac{3.34 \cdot 10^{-5} F \cdot n}{a_E \cdot (D_o - D_i) \cdot a_T \cdot a_M \cdot a_B} \quad [\text{MPa} \times \text{m/s}]$$

For oscillating movement, calculate the average rotational speed.

$$(4.4.8) \quad n = \frac{4\varphi \cdot n_{osc}}{360} \quad [1/\text{min}]$$

Estimation of bearing life L_H

Bushes (Steady load)

$$(4.4.9) \quad L_H = \frac{265}{pv} - a_L \quad [\text{h}]$$

Bushes (Rotating load)

$$(4.4.10) \quad L_H = \frac{530}{pv} - a_L \quad [\text{h}]$$

Flanged Bushes (Axial load)

(4.4.11) [h]

$$L_H = \frac{175}{pv} - a_L$$

a_L see Table 11, Page 18

Thrust Washers

(4.4.12) [h]

$$L_H = \frac{175}{pv} - a_L$$

Bore Burnishing

If the DP4 bush is bore burnished then this must be allowed for in estimating the bearing life by the application factor a_C (Table 12, Page 19).

Estimated Bearing Life

(4.4.13) [h]

$$L_H = L_H \cdot a_C$$

a_C see Table 12, Page 19

For Oscillating Movements or Dynamic loads

Calculate estimated number of cycles Z_T

(4.4.14) [cycles]

$$Z_T = L_H \cdot n_{osc} \cdot 60$$

If the required bearing life is known, the total number of cycles can be determined.

Check that Z_T is less than total number of cycles Q for the operating specific load p_{lim} (Table 8, Page 16).

If $Z_T < Q$, bearing life will be limited by wear after Z_T cycles.

If $Z_T > Q$, bearing life will be limited by fatigue after Z_T cycles.

(4.4.15) [cycles]

$$Z_T = L_H \cdot C \cdot 60$$

Slideways

Specific load factor

(4.4.16) [-]

$$a_{E1} = A - \frac{F}{p_{lim}}$$

If negative the bearing is overloaded and the bearing area should be increased.

Speed, temperature and material application factor

(4.4.17) [-]

$$a_{E2} = \frac{280 \cdot a_T \cdot a_M}{F \cdot v}$$

a_T see Table 10, Page 17
 a_M see Table 11, Page 18

Relative contact area factor

(4.4.18) [-]

$$a_{E3} = \frac{A}{A_M}$$

Estimated bearing life

(4.4.19) [-]

$$L_H = a_{E1} \cdot a_{E2} \cdot a_{E3} - a_L$$

Note:

Estimated bearing lives greater than 4000 hours are subject to error due to inaccuracies in the extrapolation of test data.

4 Bearing Performance

4.5 Worked Examples

Cylindrical Bush

Given:			
Load Details	Steady Load	Inside Diameter D_i	40 mm
	Continuous Rotation	Length B	30 mm
Shaft	Steel	Bearing Load F	5000 N
	Unlubricated at 25 °C	Rotational Speed n	25 1/min

Calculation Constants and Application Factors			
Specific Load Limit p_{lim}	140 MPa	(Table 8, Page 16)	
Application Factor a_T	1.0	(Table 10, Page 17)	
Material Application Factor a_M	1.0	(Table 11, Page 18)	
Bearing Size Factor a_B	0.85	(Fig. 21, Page 19)	
Life Correction Constant a_L	400	(Table 11, Page 18)	

Calculation	Ref	Value
Specific Load p [MPa]	(4.4.1), Page 20	$p = \frac{F}{D_i \cdot B} = \frac{5000}{40 \cdot 30} = 4.17$
Sliding Speed v [m/s]	(4.3.5), Page 16	$v = \frac{D_i \cdot \pi \cdot n}{60 \cdot 10^3} = \frac{40 \cdot 3.14 \cdot 25}{60 \cdot 10^3} = 0.052$
High Load Factor a_E [-] (must be >0)	(4.4.4), Page 20	$a_E = \frac{p_{lim} - p}{p_{lim}} = \frac{140 - 4.17}{140} = 0.97$
Modified pv Factor [MPa x m/s]	(4.4.5), Page 20	$pv = \frac{5.25 \cdot 10^{-5} \cdot F \cdot n}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = \frac{6.5625}{24.265} = 0.27$
Life L_H [h]	(4.4.9), Page 20	$L_H = \frac{265}{pv} \cdot a_L = \frac{265}{0.27} \cdot 400 = 581$

Thrust washer

Given:			
Load Details	Axial Load	Inside Diameter D_i	38 mm
	Continuous Rotation	Outside Diameter D_o	62 mm
Shaft	Steel	Bearing Load F	6500 N
	Unlubricated at 25 °C	Rotational Speed n	10 1/min

Calculation Constants and Application Factors			
Specific Load Limit p_{lim}	140 MPa	(Table 8, Page 16)	
Application Factor a_T	1.0	(Table 10, Page 17)	
Material Application Factor a_M	1.0	(Table 11, Page 18)	
Bearing Size Factor a_B	0.85	(Fig. 21, Page 19)	
Life Correction Constant a_L	400	(Table 11, Page 18)	

Calculation	Ref	Value
Specific Load p [MPa]	(4.4.3), Page 20	$p = \frac{4 \cdot F}{\pi \cdot (D_o^2 - D_i^2)} = \frac{4 \cdot 6500}{\pi \cdot (62^2 - 38^2)} = 3.45$
Sliding Speed v [m/s]	(4.3.6), Page 16	$v = \frac{D_o + D_i}{2} \cdot \pi \cdot n = \frac{62 + 38}{2} \cdot \pi \cdot 10 = \frac{2}{60 \cdot 10^3} = 0.026$
High Load Factor a_E [-] (must be >0)	(4.4.4), Page 20	$a_E = \frac{p_{lim} - p}{p_{lim}} = \frac{140 - 3.45}{140} = 0.975$
Modified pv Factor [MPa x m/s]	(4.4.7), Page 20	$pv = \frac{3.34 \cdot 10^{-5} \cdot F \cdot n}{a_E \cdot (D_o - D_i) \cdot a_T \cdot a_M \cdot a_B} = \frac{2.171}{19.28} = 0.113$
Life L_H [h]	(4.4.12), Page 21	$L_H = \frac{175}{pv} \cdot a_L = \frac{175}{0.113} \cdot 400 = 1149$

Flanged Bush

Given:			
Load Details	Axial Load	Flange Outside Diameter D_{fl}	23 mm
	Continuous Rotation	Inside Diameter D_i	15 mm
Shaft	Steel	Bearing Load F	250 N
	Unlubricated at 25 °C	Rotational Speed n	5 1/min

Calculation Constants and Application Factors			
Specific Load Limit p_{lim}	140 MPa	(Table 8, Page 16)	
Application Factor a_T	1.0	(Table 10, Page 17)	
Material Application Factor a_M	1.0	(Table 11, Page 18)	
Bearing Size Factor a_B	1.0	(Fig. 21, Page 19)	
Life Correction Constant a_L	400	(Table 11, Page 18)	

Calculation	Ref	Value
Specific Load p [MPa]	(4.4.2), Page 20	$p = \frac{F}{0.04 \cdot (D_{fl}^2 - D_i^2)} = \frac{250}{0.04 \cdot (23^2 - 15^2)} = 20.55$
Sliding Speed v [m/s]	(4.3.6), Page 16	$v = \frac{D_{fl} + D_i}{2} \cdot \pi \cdot n = \frac{23 + 15}{2} \cdot \pi \cdot 5 = \frac{3.14 \cdot 5}{60 \cdot 10^3} = 0.005$
High Load Factor a_E [-] (must be >0)	(4.4.4), Page 20	$a_E = \frac{p_{lim} - p}{p_{lim}} = \frac{140 - 20.55}{140} = 0.0853$
Modified pv Factor [MPa x m/s]	(4.4.6), Page 20	$pv = \frac{6.5 \cdot 10^{-4} \cdot F \cdot n}{a_E \cdot (D_{fl} - D_i) \cdot a_T \cdot a_M \cdot a_B} = \frac{0.8125}{6.82} = 0.119$
Life L_H [h]	(4.4.11), Page 21	$L_H = \frac{175}{pv} \cdot a_L = \frac{175}{0.119} \cdot 400 = 1071$

5 Lubrication

DP4 provides excellent performance in lubricated applications. The following sections describe the basics of lubrication

and provide guidance on the application of DP4 in such environments.

5.1 Lubricants

DP4 can be used with most fluids including:

- water
- lubricating oils
- engine oil

In general, the fluid will be acceptable if it does not chemically attack the filled PTFE overlay or the porous bronze interlayer.

Where there is doubt about the suitability of a fluid, a simple test is to submerge a sample of DP4 material in the fluid for two to three weeks at 15-20 °C above the operating temperature.

- turbine oil
- hydraulic fluid
- solvent
- refrigerants

The following will usually indicate that the fluid is not suitable for use with DP4:

- A significant change in the thickness of the DP4 material,
- A visible change in the bearing surface other than some discolouration or staining,
- A visible change in the microstructure of the bronze interlayer.

5.2 Tribology

There are three modes of lubricated bearing operation which relate to the thickness of the developed lubricant film between the bearing and the mating surface:

- Hydrodynamic lubrication
- Mixed film lubrication
- Boundary lubrication.

These three modes of operation depend upon:

- Bearing dimensions
- Clearance
- Load
- Speed
- Lubricant Viscosity
- Lubricant Flow

Hydrodynamic lubrication

Characterised by:

- Complete separation of the shaft from the bearing by the lubricant film
- Very low friction and no wear of the bearing or shaft since there is no contact
- Coefficients of friction of 0.001 to 0.01

Hydrodynamic conditions occur when

$$(5.2.1) \quad p \leq \frac{v \cdot \eta}{7.5} \cdot \frac{B}{D_i} \quad [\text{MPa}]$$

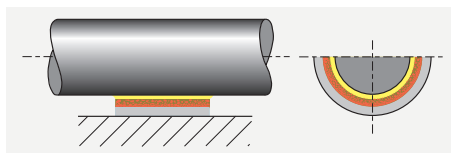


Fig. 24: Hydrodynamic lubrication

Mixed film lubrication

Characterised by:

- Combination of hydrodynamic and boundary lubrication.
- Part of the load is carried by localised areas of self pressurised lubricant and the remainder supported by boundary lubrication.
- Friction and wear depend upon the degree of hydrodynamic support developed.

- DP4 provides low friction and high wear resistance to support the boundary lubricated element of the load.

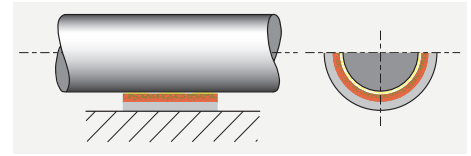


Fig. 25: Mixed film lubrication

Boundary lubrication

Characterised by:

- Rubbing of the shaft against the bearing with virtually no lubricant separating the two surfaces.
- Bearing material selection is critical to performance.
- Shaft wear is likely due to contact between bearing and shaft.
- The excellent properties of DP4 material minimises wear under these conditions.
- The dynamic coefficient of friction with DP4 is typically 0.05 to 0.3 under boundary lubrication conditions.

- The static coefficient of friction with DP4 is typically slightly above the dynamic coefficient of friction under boundary lubrication conditions.

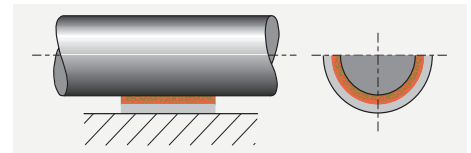


Fig. 26: Boundary lubrication

5.3 Characteristics of Lubricated Bearings

DP4 is particularly effective in the most demanding of lubricated applications

- **High load conditions**
In highly loaded applications operating under boundary or mixed film conditions DP4 shows excellent wear resistance and low friction.
- **Start up and shut down under load**
With insufficient speed to generate a hydrodynamic film the bearing will operate under boundary or mixed film conditions.
 - DP4 minimises wear
 - DP4 requires less start-up torque than conventional metallic bearings.

Note the following however:

If a DP4 bearing is required to run dry after running in water under non hydrodynamic conditions then the wear resistance will be substantially reduced due to an increased amount of bedding in wear.

In order to use Fig. 27

- Using the formula in Section 4:
 - Calculate the specific load p ,
 - Calculate the shaft surface speed v .

where full hydrodynamic operation cannot be maintained, for example:

- **Sparse lubrication**
Many applications require the bearing to operate with less than the ideal lubricant supply, typically with splash or mist lubrication only.
DP4 requires significantly less lubricant than conventional metallic bearings.
- **Non lubricating fluids**
DP4 operates satisfactorily in low viscosity and non lubricating fluids such as water and some process fluids.

Fig. 27, Page 25 shows the three lubrication regimes discussed above plotted on a graph of sliding speed vs the ratio of specific load to lubricant viscosity.

- Using the viscosity temperature relationships presented in Table 13:
 - Determine the viscosity in centipoise of the lubricant.

Note:

Viscosity is a function of operating temperature. If the operating temperature of the fluid is unknown, a provisional temperature of 25 °C above ambient can be used.

5.4 Design Guidance

Dynamic viscosity η [cP]															
Temperature [°C]	0	10	20	30	40	50	60	70	80	90	100	110	120	130	140
Lubricant															
ISO VG 32	310	146	77	44	27	18	13	9.3	7.0	5.5	4.4	3.6	3.0	2.5	2.2
ISO VG 46	570	247	121	67	40	25	17	12	9.0	6.9	5.4	4.4	3.6	3.0	2.6
ISO VG 68	940	395	190	102	59	37	24	17	12	9.3	7.2	5.8	4.7	3.9	3.3
ISO VG 100	2110	780	335	164	89	52	33	22	15	11.3	8.6	6.7	5.3	4.3	3.6
ISO VG 150	3600	1290	540	255	134	77	48	31	21	15	11	8.8	7.0	5.6	4.6
Diesel oil	4.6	4.0	3.4	3.0	2.6	2.3	2.0	1.7	1.4	1.1	0.95				
Petrol	0.6	0.56	0.52	0.48	0.44	0.40	0.36	0.33	0.31						
Kerosene	2.0	1.7	1.5	1.3	1.1	0.95	0.85	0.75	0.65	0.60	0.55				
Water	1.79	1.30	1.0	0.84	0.69	0.55	0.48	0.41	0.34	0.32	0.28				

Table 13: Dynamic viscosity

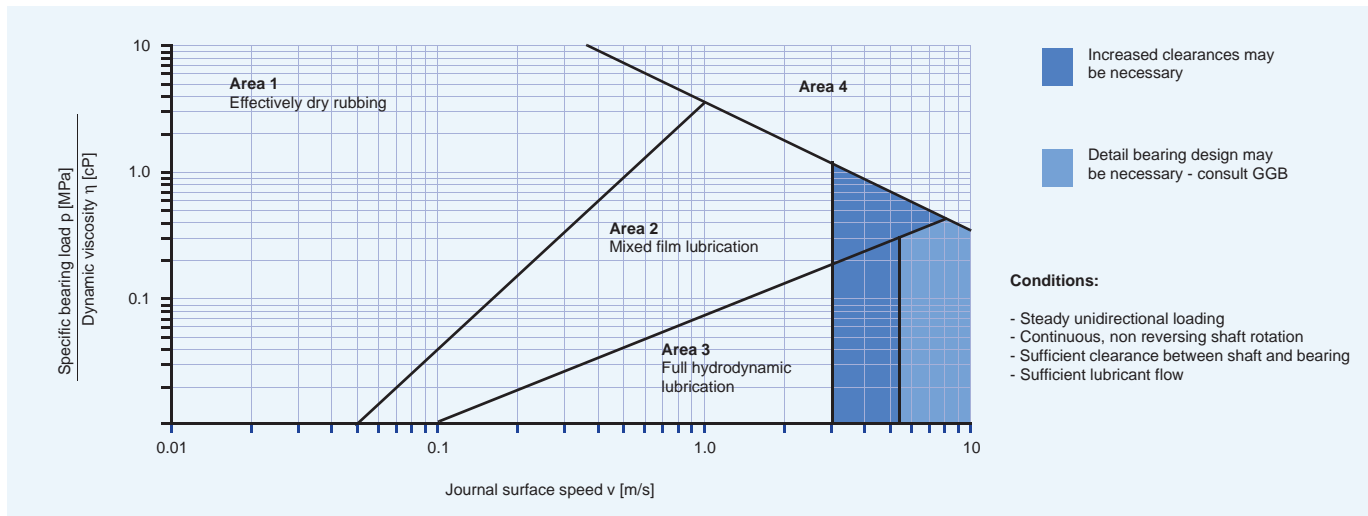


Fig. 27: Design guide for lubricated application

Explanation to Fig. 27

Area 1

The bearing will operate with boundary lubrication and p_v factor will be the major determinant of bearing life. DP4 bearing performance can be calculated using the

method given in Section 4, although the result will probably underestimate the bearing life.

Area 2

The bearing will operate with mixed film lubrication and p_v factor is no longer a significant parameter in determining the

bearing life. DP4 bearing performance will depend upon the nature of the fluid and the actual service conditions.

Area 3

The bearing will operate with hydrodynamic lubrication. Bearing wear will be determined only by the cleanliness of the

lubricant and the frequency of start up and shut down.

Area 4

These are the most demanding operating conditions. The bearing is operated under either high speed or high bearing load to viscosity ratio, or, a combination of both.

These conditions may cause

- excessive operating temperature and/or
- high wear rate.

Bearing performance may be improved by the addition of one or more grooves to the bearing and a shaft surface finish $<0.05 \mu\text{m } R_a$.

5.5 Clearances for lubricated operation

The recommended shaft and housing diameters given for standard DP4 bushes will provide sufficient clearance for applications operating with boundary lubrication.

For bearings operating with mixed film or hydrodynamic lubrication it may be

necessary to improve the fluid flow through the bearing by reducing the recommended shaft diameter by approximately 0.1 %, particularly when the shaft surface speed exceeds 2.5 m/s.

5.6 Grooving for lubricated operation

In demanding applications an axial oil groove will improve the performance of DP4. Fig. 28 shows the recommended form and location of a single groove with

respect to the applied load and the bearing split. GGB can manufacture special DP4 bearings with embossed or milled grooves on request.

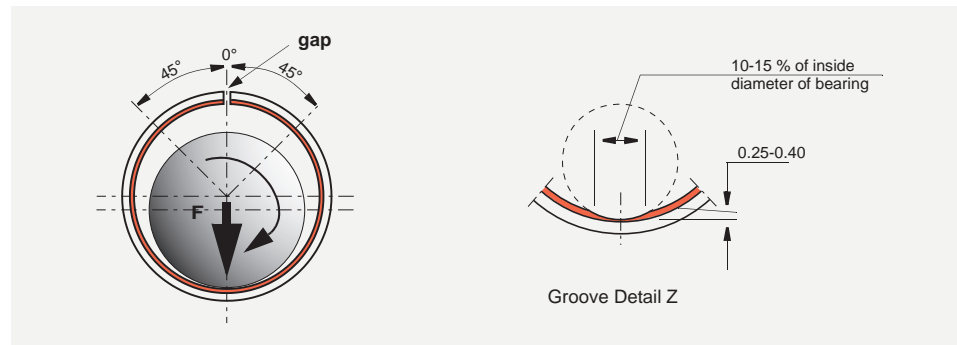


Fig. 28: Location of grooves

5.7 Mating Surface Finish for lubricated operation

- $R_a = 0.4 \pm 0.1 \mu\text{m}$ Boundary lubrication
- $R_a = 0.1 - 0.2 \mu\text{m}$ Mixed film or hydrodynamic conditions
- $R_a \leq 0.05 \mu\text{m}$ for the most demanding operating conditions.

5.8 Grease Lubrication

DP4 is not generally recommended for use with grease lubrication. In particular the following must be avoided:

- Dynamic loads - which can result in erosion of the PTFE bearing surface.
- Greases with EP additives or fillers such as graphite or MoS_2 which can cause rapid wear of DP4.

Under grease lubrication, improved performance can be obtained by the use of other GGB metal polymer bearing materials, for example, DX[®], DX[®]10 with DuraStrong[™] technology, DS[™], HX[™].

Please contact your local sales representative or consult www.ggbearings.com for more details.

6 Bearing Assembly

Dimensions and Tolerances

DP4 bushes are prefinished and excluding very exceptional circumstances, must not be broached, machined or otherwise modified in the bore. It is essential that the correct running clearance is used and that both the diameter of the shaft and the bore of the housing are finished to the limits given in the tables. Under dry running conditions any increase in the clearances given will result in a proportional reduction in performance.

If the bearing housing is unusually flexible the bush will not close in by the calculated

amount and the running clearance will be more than the optimum. In these circumstances the housing should be bored slightly undersize or the journal diameter increased, the correct size being determined by experiment.

Where free running is essential, or where light loads (less than 0.1 MPa) prevail and the available torque is low, increased clearance is required and it is recommended that the shaft size quoted in the table be reduced by 0.025 mm.

6.1 Allowance for Thermal Expansion

For operation in high temperature environments the clearance should be increased by the amounts indicated by Fig. 29 to

compensate for the inward thermal expansion of the bearing lining.

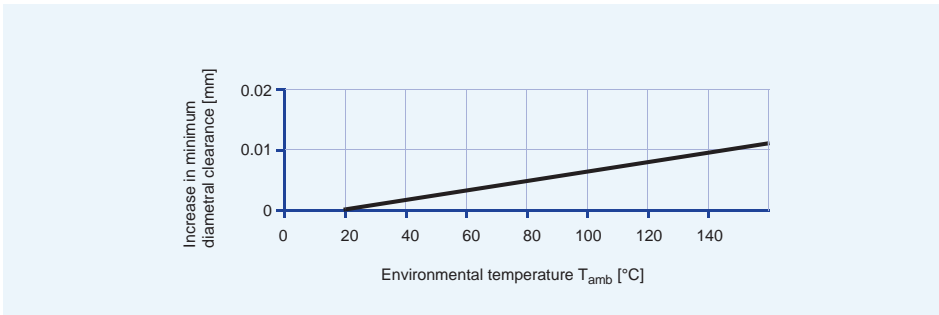


Fig. 29: Increase in diametral clearance

If the housing is non-ferrous then the bore should be reduced by the amounts given in Table 14, in order to give an increased

interference fit to the bush, with a similar reduction in the journal diameter additional to that indicated by Fig. 29.

Housing material	Reduction in housing diameter per 100 °C rise	Reduction in shaft diameter per 100 °C rise
Aluminium alloys	0.1 %	0.1 % + values from Fig. 29
Copper base alloys	0.05 %	0.05 % + values from Fig. 29
Steel and cast iron	–	values from Fig. 29
Zinc base alloys	0.15 %	0.15 % + values from Fig. 29

Table 14: Allowance for high temperature

6.2 Tolerances for minimum clearance

Where it is required to keep the variation of assembled clearance to a minimum, closer tolerances can be specified towards the

upper end of the journal tolerance and the lower end of the housing tolerance.

If housings to H6 tolerance are used, then the journals should be finished to the following limits.

D_i	D_j
>5 mm <25 mm	-0.019 to -0.029
>25 mm < 50 mm	-0.021 to -0.035

Table 15: Shaft tolerances for use with H6 housings

The sizes in Table 16 give the following nominal clearance range.

D_i	C_D
10 mm	0,009 to 0,080
50 mm	0,011 to 0,134

Table 16: Clearance vs bearing diameter

Burnishing

The burnishing of the bore of an assembled DP4 bush enables a smaller clearance variation to be obtained. Fig. 30 shows a recommended burnishing tool design for the burnishing of DP4 bushes.

The coining section of the burnishing tool should be case hardened (case depth 0.6-1.2 mm, HRC 60±2) and polished with diamond paste ($R_z \approx 1 \mu\text{m}$). A TiN type surface treatment increases the wear resistance of the burnishing tool and when absent gives a visual indication of burnishing tool wear.

The reduction in bearing performance as a result of burnishing is allowed for in the bearing life calculation by the application factor a_C (Table 12, Page 19). The impact of burnishing on the bearing and assembly should be validated by trials.

Note: Ball burnishing or fine boring of DP4 bushes is not recommended.

Assembled bush Inside- \varnothing	Required bush Inside- \varnothing	Required burnishing tool- $\varnothing D_C$
$D_{i,a}$	$D_{i,a} + 0.025$	$D_{i,a} + 0.06$
$D_{i,a}$	$D_{i,a} + 0.038$	$D_{i,a} + 0.08$
$D_{i,a}$	$D_{i,a} + 0.050$	$D_{i,a} + 0.1$

Table 17: Burnishing Tool Tolerances

The values given in Table 17 indicate the dimensions of the burnishing tool required to give specific increases in the bearing bore diameter.

Exact values must be determined by test.

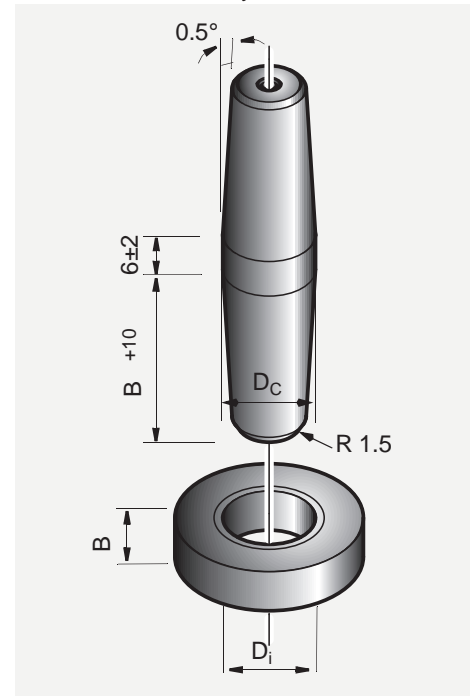


Fig. 30: Burnishing Tool

6.3 Counterface Design

The suitability of mating surface materials and recommendations of mating surface finish for use with DP4 are discussed in detail on page 16.

DP4 is normally used in conjunction with ferrous journals and thrust faces, but in damp or corrosive surroundings, particularly without the protection of oil or grease, stainless steel, hard chromium plated mild steel, or hard anodised aluminium is recommended. When plated mating surfaces are specified the plating should possess adequate strength and adhesion,

particularly if the bearing is to operate with high fluctuating loads.

The shaft or thrust collar used in conjunction with the DP4 bush or thrust washer must extend beyond the bearing surface in order to avoid cutting into it. The mating surface must also be free from grooves or flats, the end of the shaft should be given a lead-in chamfer and all sharp edges or projections which may damage the soft overlay of the DP4 must be removed.

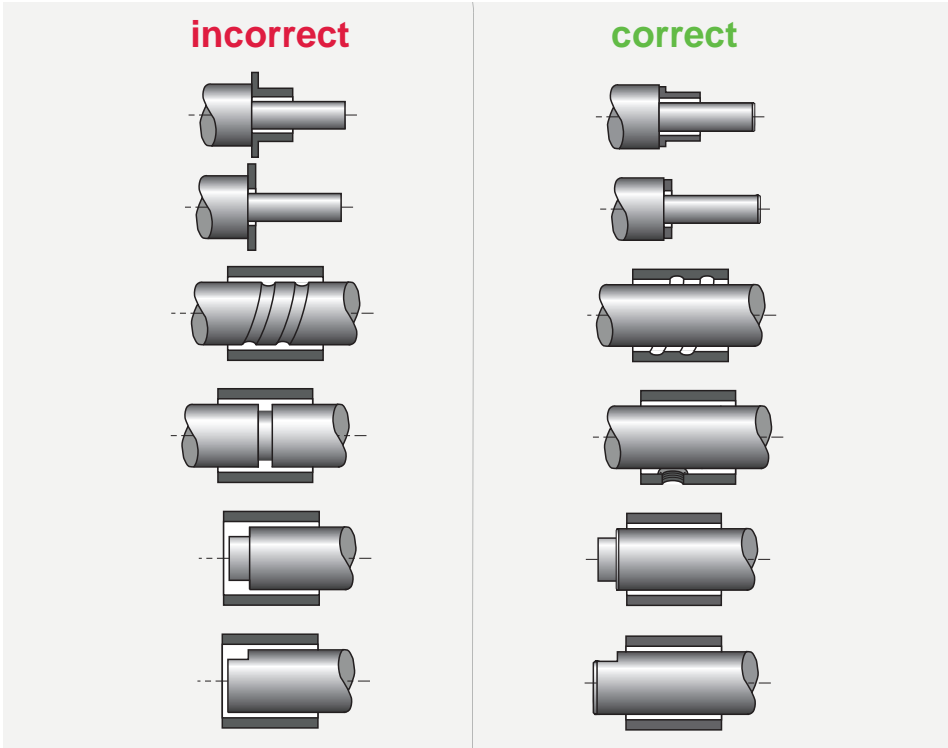


Fig. 31: Counterface design

6.4 Installation

Fitting of cylindrical Bushes

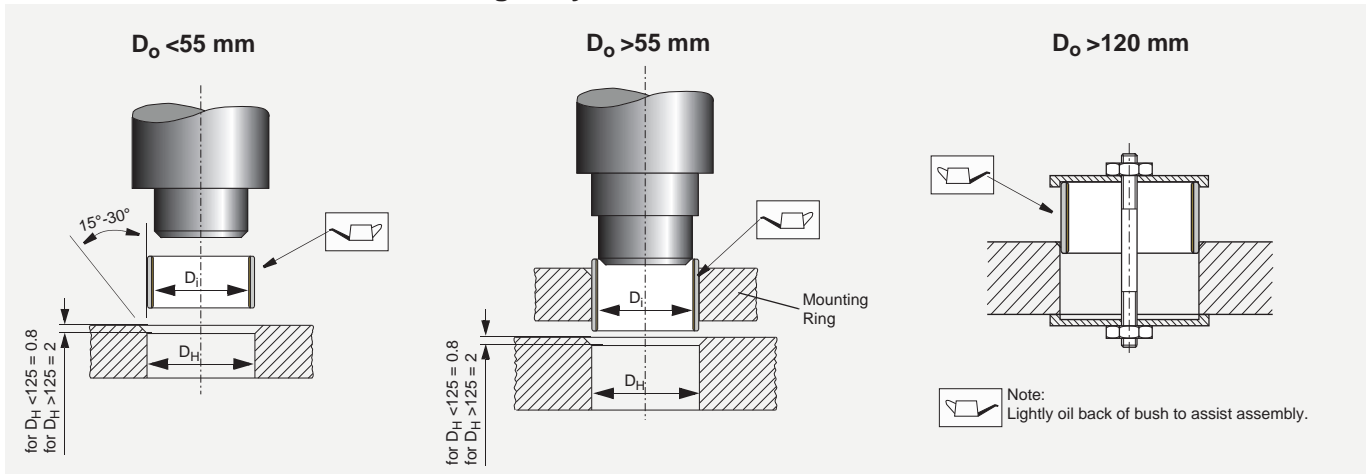


Fig. 32: Fitting of cylindrical bushes

Fitting of flanged bushes

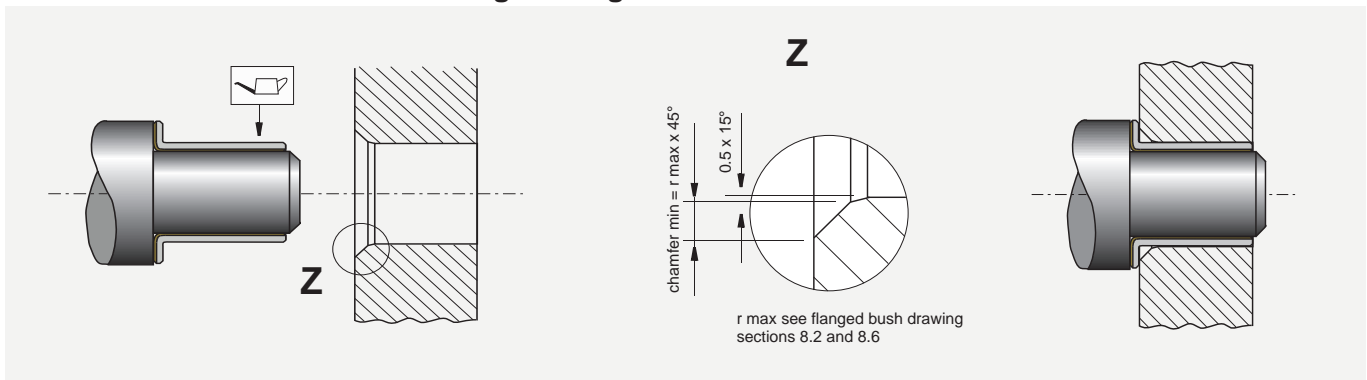


Fig. 33: Fitting of flanged bushes

Insertion Forces

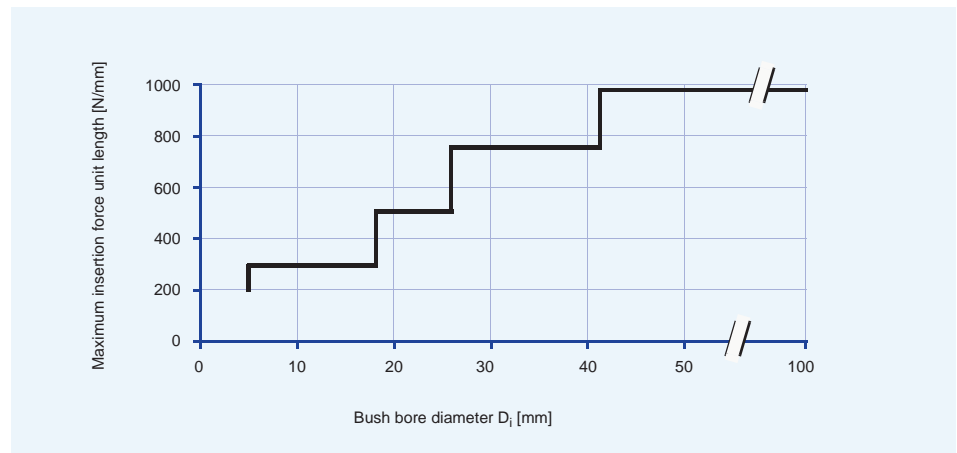


Fig. 34: Maximum insertion force F_i

Alignment

Accurate alignment is an important consideration for all bearing assemblies. With DP4 bearings misalignment over the

length of a bush (or pair of bushes), or over the diameter of a thrust washer should not exceed 0.020 mm as illustrated in Fig. 35.

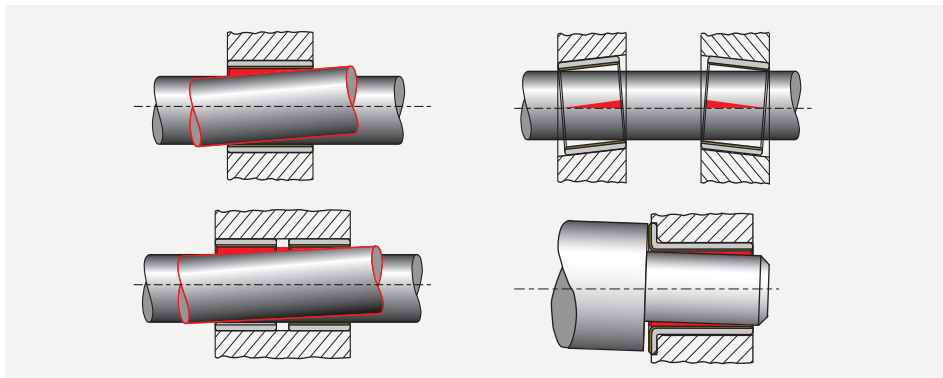


Fig. 35: Alignment

Sealing

While DP4 can tolerate the ingress of some contaminant materials into the bearing without loss of performance, where there is the possibility of highly

abrasive material entering the bearing, a suitable sealing arrangement, as illustrated in Fig. 36 should be provided.

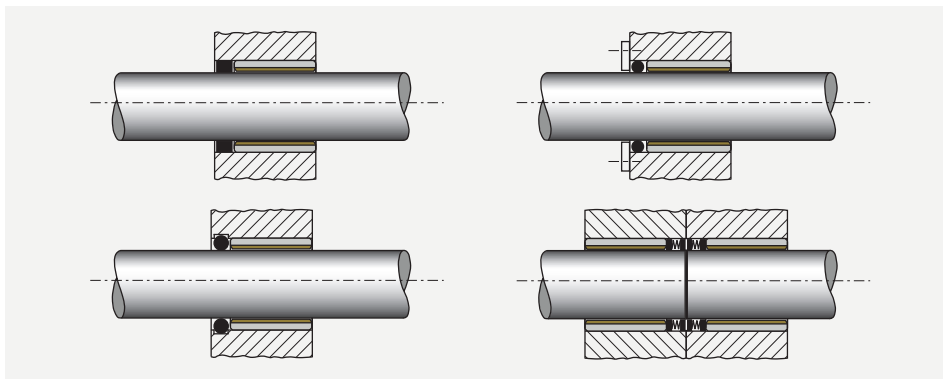


Fig. 36: Recommended sealing arrangements

6.5 Axial Location

Where axial location is necessary, it is advisable to fit DP4 thrust washers in

conjunction with DP4 bushes, even when the axial loads are low.

Fitting of Thrust Washers

DP4 thrust washers should be located in a recess as shown in Fig. 37. For the recess diameter the tolerance class [D10] is recommended. The recess depth is given in the product tables, page 40 and following.

If a recess is not possible one of the following methods may be used:

- Two dowel pins
- Two screws
- Adhesive
- Soldering (temperature <320 °C).

Important Note

- Ensure the washer ID does not touch the shaft after assembly
- Ensure that the washer is mounted with the steel/bronze backing to the housing
- Dowel pins should be recessed 0.25 mm below the bearing surface
- Screws should be countersunk 0.25 mm below the bearing surface
- DP4 must not be heated above 320 °C
- Contact adhesive manufacturers for guidance selection of suitable adhesives
- Protect the bearing surface to prevent contact with adhesive.

Grooves for Wear Debris Removal

Tests with thrust washers have demonstrated that for optimum dry wear performance at specific loads in excess of 35 MPa, four wear debris removal grooves should be machined in the bearing surface as shown in Fig. 38.

Grooves in bushes have not been found to be beneficial in this respect.

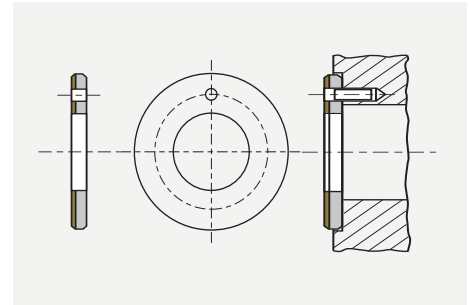


Fig. 37: Installation of Thrust-Washer

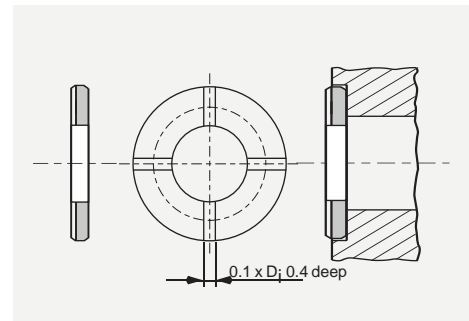


Fig. 38: Debris removal Grooves

Slideways

DP4 strip material for use as slideway bearings should be installed using one of the following methods:

- Countersunk screws
- Adhesives
- Mechanical location as shown in Fig. 39.

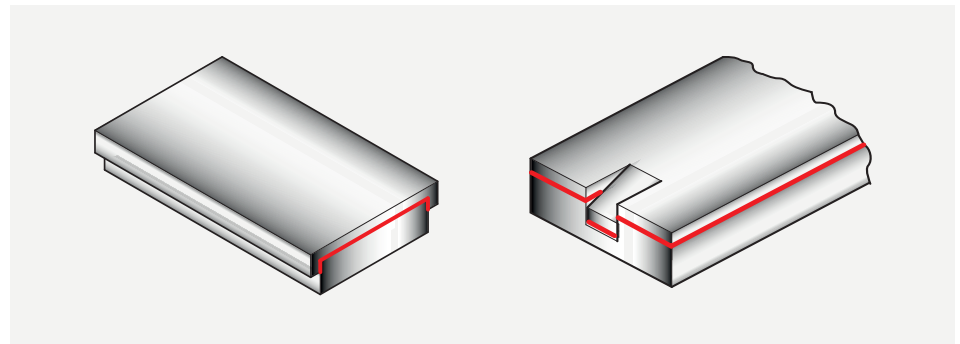


Fig. 39: Mechanical location of DP4 slideplates

7 Modification

7.1 Cutting and Machining

The modification of DP4 bearing components requires no special procedures. In general it is more satisfactory to perform machining or drilling operations from the PTFE side in order to avoid burrs. When cutting is done from the steel side, the

minimum cutting pressure should be used and care taken to ensure that any steel or bronze particles protruding into the remaining bearing material, and all burrs, are removed.

Drilling Oil Holes

Bushes should be adequately supported during the drilling operation to ensure that

no distortion is caused by the drilling pressure.

Cutting Strip Material

DP4 strip material may be cut to size by any one of the following methods.

Care must be taken to protect the bearing surface from damage and to ensure that no deformation of the strip occurs:

- Using side and face cutter, or slitting saw, with the strip held flat and securely

on a horizontal milling machine.

- Cropping
- Guillotine (For widths less than 90 mm only)
- Water-jet cutting
- Laser cutting (see Health Warning).

7.2 Electroplating

DP4 Components

In order to provide some protection in mildly corrosive environments the steel back and end faces of standard range DP4 bearings are tin flashed.

DP4 can be electroplated with most of the conventional electroplating metals including the following:

- zinc ISO 2081
- nickel ISO 1456
- hard chromium ISO 1456.



For the harder materials if the specified plating thickness exceeds approximately 5 μm then the housing diameter should be increased by twice the plating thickness in order to maintain the correct assembled bearing bore size.

Where electrolytic attack is possible tests should be conducted to ensure that all the materials in the bearing environment are mutually compatible.

8 Standard Products

8 Standard Products

8.1 DP4 Cylindrical bushes

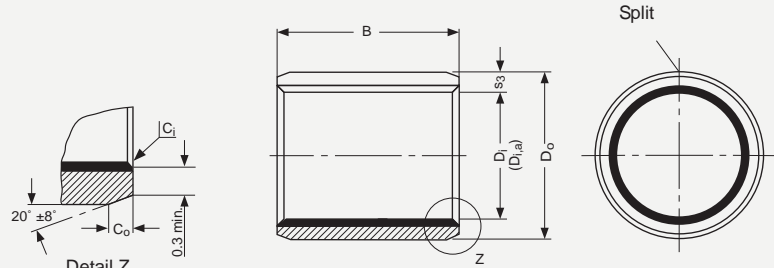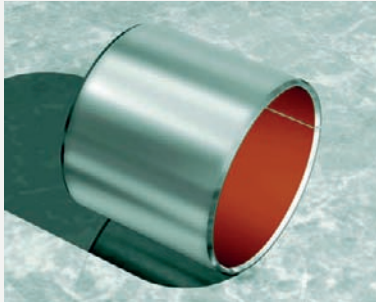

Dimensions and Tolerances according to ISO 3547 and GGB-Specifications

All dimensions in mm

Outside C_0 and Inside C_i chamfers

Wall thickness s_3	C_0 (a)		C_i (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s_3	C_0 (a)		C_i (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C_0 machined or rolled at the option of the manufacturer

b = C_i can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness s_3	Width B	Shaft- \varnothing D_j [h6, f7, h8]	Housing- \varnothing D_{H1} [H6, H7]	Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing	Clearance C_D						
	D_i	D_0							max. min.	max. min.	max. min.	max. min.		
0203DP4	2	3.5	0.750 0.730	3.25	h6	H6	2.048 2.000	0.054 0.000						
0205DP4				2.75					2.000 1.994	3.508 3.500				
0303DP4	3	4.5		3.25					h6	H6	3.048 3.000	0.054 0.000		
0305DP4				2.75									3.000 2.994	4.508 4.500
0306DP4				6.25									4.048 4.000	4.048 4.000
0403DP4	4	5.5		3.25					h6	H6	4.048 4.000	0.056 0.000		
0404DP4				4.25									4.000 3.992	5.508 5.500
0406DP4				3.75									4.048 4.000	4.048 4.000
0410DP4				6.25									4.048 4.000	4.048 4.000
0505DP4	5	7		5.25					h6	H6	5.055 4.990	0.077 0.000		
0508DP4				4.75									4.990 4.978	7.015 7.000
0510DP4				8.25									4.990 4.978	5.055 4.990
0604DP4	6	8	4.25	f7	H7	6.055 5.990	0.077 0.000							
0606DP4			3.75					5.990 5.978	8.015 8.000					
0608DP4			6.25					5.990 5.978	6.055 5.990					
0610DP4			5.75					5.990 5.978	6.055 5.990					
0705DP4	7	9	5.25	h6	H6	7.055 6.990	0.083 0.003							
0710DP4			4.75					6.987 6.972	9.015 9.000					
0710DP4			10.25					6.987 6.972	9.015 9.000					

Part No.	Nominal Diameter		Wall thickness S ₃	Width B	Shaft-Ø D _J [h6, f7, h8]	Housing-Ø D _H [H6, H7]	Bush-Ø D _{i,a} Ass. in H6/H7 housing	Clearance C _D	
	D _i	D _O							max. min.
0806DP4	8	10	1.005 0.980	6.25	7.987 7.972	10.015 10.000	8.055 7.990	0.083 0.003	
0808DP4				5.75					
0810DP4				8.25					
0812DP4				7.75					
1006DP4				10.25					
1008DP4	9.75								
1010DP4	12.25	10		12	11.75	9.987 9.972	12.018 12.000		10.058 9.990
1012DP4	6.25								
1015DP4	5.75								
1020DP4	8.25								
1208DP4	7.75								
1210DP4	10.25	12		14	9.75	11.984 11.966	14.018 14.000		12.058 11.990
1212DP4	12.25								
1215DP4	11.75								
1220DP4	15.25								
1225DP4	14.75								
1310DP4	20.25	13		15	19.75	12.984 12.966	15.018 15.000		13.058 12.990
1320DP4	10.25								
1405DP4	9.75								
1410DP4	20.25								
1412DP4	19.75								
1415DP4	5.25	14	16	4.75	13.984 13.966	16.018 16.000	14.058 13.990		
1420DP4	10.25								
1425DP4	9.75								
1510DP4	12.25								
1512DP4	11.75								
1515DP4	15.25	15	17	14.75	14.984 14.966	17.018 17.000	15.058 14.990		
1520DP4	20.25								
1525DP4	19.75								
1610DP4	25.25								
1612DP4	24.75								
1615DP4	10.25	16	18	9.75	15.984 15.966	18.018 18.000	16.058 15.990		
1620DP4	12.25								
1625DP4	11.75								
1720DP4	15.25								
	14.75								
	20.25	17	19	19.75	16.984 16.966	19.021 19.000	17.061 16.990		
	19.75								

8 Standard Products

Part No.	Nominal Diameter		Wall thickness s_3	Width B	Shaft- \varnothing D_j [h6, f7, h8]		Housing- \varnothing D_{i1} [H6, H7]		Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing	Clearance C_D
	D_i	D_o			max. min.	max. min.	max. min.	max. min.		
1810DP4	18	20	1.005 0.980	10.25	17.984 17.966	20.021 20.000	18.061 17.990	0.095 0.006		
1815DP4				9.75						
1820DP4				15.25 14.75						
1825DP4				20.25 19.75						
2010DP4	20	23	1.505 1.475	10.25	19.980 19.959	23.021 23.000	20.071 19.990	0.112 0.010		
2015DP4				9.75						
2020DP4				15.25 14.75						
2025DP4				20.25 19.75						
2030DP4	22	25	1.505 1.475	25.25	21.980 21.959	25.021 25.000	22.071 21.990	0.112 0.010		
2215DP4				24.75						
2220DP4				30.25 29.75						
2225DP4				15.25 14.75						
2230DP4	24	27	1.505 1.475	20.25	23.980 23.959	27.021 27.000	24.071 23.990	0.112 0.010		
2415DP4				19.75						
2420DP4				25.25 24.75						
2425DP4				30.25 29.75						
2430DP4	25	28	1.505 1.475	15.25	24.980 24.959	28.021 28.000	25.071 24.990	0.112 0.010		
2515DP4				14.75						
2520DP4				20.25 19.75						
2525DP4				25.25 24.75						
2530DP4	28	32	1.505 1.475	30.25	27.980 27.959	32.025 32.000	28.085 27.990	0.112 0.010		
2550DP4				29.75						
2815DP4				15.25 14.75						
2820DP4				20.25 19.75						
2825DP4	30	34	2.005 1.970	25.25	29.980 29.959	34.025 34.000	30.085 29.990	0.126 0.010		
2830DP4				24.75						
3010DP4				30.25 29.75						
3015DP4				10.25 9.75						
3020DP4	32	36	2.005 1.970	15.25	31.975 31.950	36.025 36.000	32.085 31.990	0.135 0.015		
3025DP4				14.75						
3030DP4				20.25 19.75						
3030DP4				25.25 24.75						
3040DP4	32	36	2.005 1.970	30.25	31.975 31.950	36.025 36.000	32.085 31.990	0.135 0.015		
3040DP4				29.75						
3220DP4				40.25 39.75						
3220DP4	32	36	2.005 1.970	20.25	31.975 31.950	36.025 36.000	32.085 31.990	0.135 0.015		
3230DP4				19.75						
3240DP4				30.25 29.75						
3240DP4	32	36	2.005 1.970	40.25	31.975 31.950	36.025 36.000	32.085 31.990	0.135 0.015		
3240DP4				39.75						

Part No.	Nominal Diameter		Wall thickness S ₃	Width B	Shaft-Ø D _J [h6, f7, h8]	Housing-Ø D _H [H6, H7]	Bush-Ø D _{i,a} Ass. in H6/H7 housing	Clearance C _D				
	D _i	D _O							max. min.	max. min.	max. min.	max. min.
3520DP4	35	39	2.005 1.970	20.25	34.975 34.950	39.025 39.000	35.085 34.990	0.135 0.015				
3530DP4				19.75								
3535DP4				30.25								
3540DP4				29.75								
3550DP4				35.25								
3720DP4	37	41		34.75					36.975	41.025	37.085	0.135 0.015
4020DP4				40.25					36.950	41.000	36.990	
4030DP4	40	44		19.75					39.975 39.950	44.025 44.000	40.085 39.990	0.135 0.015
4040DP4				20.25								
4050DP4				30.25								
4520DP4			29.75									
4530DP4	45	50	2.505 2.460	40.25	44.975 44.950	50.025 50.000	45.105 44.990	0.155 0.015				
4540DP4				39.75								
4545DP4				45.25								
4550DP4				44.75								
5020DP4				50.25								
5030DP4	49.75	50		55	20.25	49.975 49.950	55.030 55.000	50.110 49.990	0.160 0.015			
5040DP4	19.75											
5050DP4	30.25											
5060DP4	29.75											
5520DP4	40.25											
5525DP4	39.75	55		60	20.25	54.970 54.940	60.030 60.000	55.110 54.990	0.170 0.020			
5530DP4	19.75											
5540DP4	25.25											
5550DP4	24.75											
5555DP4	30.25											
5560DP4	29.75											
6020DP4	40.25											
6030DP4	39.75											
6040DP4	50.25	60	65	20.25	59.970 59.940	65.030 65.000	60.110 59.990	0.170 0.020				
6050DP4	19.75											
6060DP4	30.25											
6070DP4	29.75											
	40.25											


8 Standard Products

Part No.	Nominal Diameter		Wall thickness S ₃	Width B	Shaft-∅ D _J [h6, f7, h8]		Housing-∅ D _H [H6, H7]		Bush-∅ D _{i,a} Ass. in H6/H7 housing	Clearance C _D
	D _i	D _O			max. min.	max. min.	max. min.	max. min.		
6530DP4	65	70	2.505 2.460	30.25	f7	64.970 64.940	70.030 70.000	65.110 64.990	0.170 0.020	
6550DP4				29.75						50.25
6570DP4				49.75						70.25
7040DP4	70	75		40.25		69.970 69.940	75.030 75.000	70.110 69.990		
7050DP4				39.75						50.25
7070DP4				49.75						70.25
7560DP4	75	80		60.25		74.970 74.940	80.030 80.000	75.110 74.990		
7580DP4				59.75						80.25
8040DP4				79.75						40.50
8060DP4	80	85		39.50		80.000 79.946	85.035 85.000	80.155 80.020		
8080DP4				60.50						80.50
80100DP4				59.50						79.50
8530DP4	85	90	100.50	85.000 84.946	90.035 90.000	85.155 85.020				
8560DP4			99.50				60.50			
85100DP4			99.50				59.50			
9060DP4	90	95	100.50	90.000 89.946	95.035 95.000	90.155 90.020				
90100DP4			99.50				60.50			
9560DP4			99.50				59.50			
9560DP4	95	100	100.50	95.000 94.946	100.035 100.000	95.155 95.020				
95100DP4			99.50				60.50			
10050DP4			99.50				50.50			
10060DP4	100	105	49.50	100.000 99.946	105.035 105.000	100.155 100.020				
100115DP4			60.50				60.50			
10560DP4			59.50				59.50			
105115DP4	105	110	115.50	105.000 104.946	110.035 110.000	105.155 105.020				
11060DP4			114.50				60.50			
110115DP4			114.50				59.50			
11550DP4	115	120	114.50	110.000 109.946	115.035 115.000	110.155 110.020				
11570DP4			50.50				60.50			
12050DP4			49.50				59.50			
12050DP4	120	125	69.50	115.000 114.946	120.035 120.000	115.155 115.020				
12060DP4			50.50				60.50			
120100DP4			49.50				59.50			
125100DP4	125	130	100.50	120.000 119.946	125.040 125.000	120.210 120.070				
13060DP4			99.50				100.50			
130100DP4			99.50				100.50			
13060DP4	130	135	100.50	125.000 124.937	130.040 130.000	125.210 125.070				
130100DP4			99.50				60.50			
			99.50				59.50			

Part No.	Nominal Diameter		Wall thickness s_3	Width B	Shaft- \varnothing D_j [h6, f7, h8]	Housing- \varnothing D_{i1} [H6, H7]	Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing	Clearance C_D	
	D_i	D_o	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	
13560DP4	135	140	2.465 2.415	60.50	135.000 134.937	140.040 140.000	135.210 135.070	0.273 0.070	
13580DP4				59.50					
14060DP4	140	145		60.50	140.000 139.937	145.040 145.000	140.210 140.070		
140100DP4				59.50					
15060DP4	150	155		60.50	150.000 149.937	155.040 155.000	150.210 150.070		
15080DP4				59.50					
150100DP4				80.50					
16080DP4				79.50					
160100DP4	160	165		100.50	160.000 159.937	165.040 165.000	160.210 160.070		
180100DP4				99.50					
200100DP4	180	185		100.50 99.50	180.000	185.046 185.000	180.216 180.070		0.279 0.070
210100DP4	200	205			179.937				
220100DP4	210	215			200.000	205.046 205.000	210.216 210.070		0.288 0.070
250100DP4					199.928				
300100DP4	250	255			210.000	225.046 225.000	220.216 220.070		
13560DP4					209.928				
13580DP4			220.000						
14060DP4			219.928						
140100DP4	220	225	250.000	255.052 255.000	250.222 250.070	0.294 0.070			
15060DP4			249.928						
15080DP4	250	255	300.000	305.052 305.000	300.222 300.070	0.303 0.070			
150100DP4			299.919						

8 Standard Products

8.2 DP4 Flanged bushes

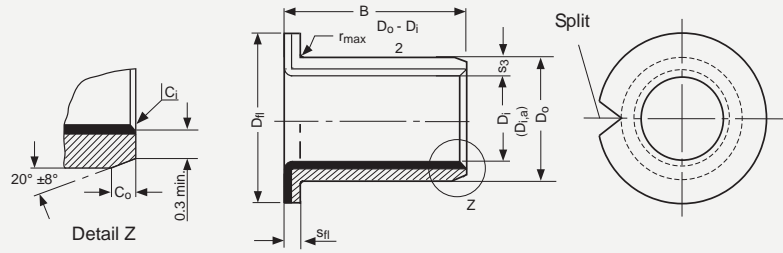

Dimensions and Tolerances according to ISO 3547 and GGB-Specifications

All dimensions in mm

Outside C_0 and Inside C_i chamfers

Wall thickness s_3	C_0 (a)		C_i (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s_3	C_0 (a)		C_i (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C_0 machined or rolled at the option of the manufacturer



b = C_i can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness s_3	Flange thickness s_{ij}	Flange- \varnothing D_{II}	Width B	Shaft- \varnothing D_J [h6, f7]	Housing- \varnothing D_{H1} [H6, H7]	Bush- \varnothing $D_{I,a}$ Ass. in H6/H7 housing	Clearance C_D
	D_i	D_o								
BB0304DP4	3	4.5	0.750 0.730	0.80 0.70	7.50 6.50	4.25 3.75	h6 2.994	H6 4.508	3.048 3.000	0.054 0.000
BB0404DP4	4	5.5			9.50 8.50					
BB0505DP4	5	7	1.005 0.980	1.05 0.80	10.50 9.50	5.25 4.75	f7 4.990 4.978	H7 7.015 7.000	5.055 4.990	0.077 0.000
BB0604DP4	6	8			12.50 11.50	4.25 3.75				
BB0806DP4			8	10	15.50 14.50	5.75 5.25	7.987 7.972	10.015 10.000	8.055 7.990	0.083 0.003
BB0808DP4	7.75 7.25									
BB0810DP4	9.75 9.25									
BB1007DP4	10	12	18.50 17.50	7.25 6.75	f7 9.987 9.972	H7 12.018 12.000	10.058 9.990	0.086 0.003		
BB1009DP4				9.25 8.75						
BB1012DP4				12.25 11.75						
BB1017DP4				17.25 16.75						
BB1207DP4	12	14	20.50 19.50	7.25 6.75	11.984 11.966	H7 14.018 14.000	12.058 11.990	0.092 0.006		
BB1209DP4				9.25 8.75						
BB1212DP4				12.25 11.75						
BB1217DP4				17.25 16.75						

Part No.	Nominal Diameter		Wall thickness S ₃	Flange thickness S _{fl}	Flange-∅ D _{fl}	Width B	Shaft-∅ D _J [h6, f7]	Housing-∅ D _H [H6, H7]	Bush-∅ D _{1,a} Ass. in H6/H7 housing	Clearance C _D				
	D _i	D _o	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.				
BB1412DP4	14	16	1.005 0.980	1.05 0.80	22.50 21.50	12.25	13.984 13.966	16.018 16.000	14.058 13.990	0.092 0.006				
BB1417DP4						11.75								
BB1509DP4	15	17			23.50 22.50	9.25	14.984 14.966		17.018 17.000		15.058 14.990			
BB1512DP4						8.75								
BB1517DP4						12.25 11.75								
BB1612DP4	16	18			24.50 23.50	12.25	15.984 15.966		18.018 18.000		16.058 15.990			
BB1617DP4						11.75								
BB1812DP4	18	20			26.50 25.50	12.25	17.984 17.966		20.021 20.000		18.061 17.990			
BB1817DP4						11.75								
BB1822DP4						17.25 16.75								
BB2012DP4	20	23			1.505 1.475	1.60 1.30	30.50 29.50		11.75		19.980 19.959	23.021 23.000	20.071 19.990	0.112 0.010
BB2017DP4									11.25					
BB2022DP4			16.75 16.25											
BB2512DP4			21.75 21.25											
BB2517DP4			11.75 11.25											
BB2522DP4	25	28	35.50 34.50	16.75	24.980 24.959	28.021 28.000	25.071 24.990							
BB3016DP4				16.25										
BB3026DP4	30	34	2.005 1.970	2.10 1.80	42.50	29.980 29.959	34.025 34.000	30.085 29.990	0.126 0.010					
BB3516DP4					15.75									
BB3526DP4	35	39			47.50 46.50	26.25	34.975 34.950	39.025 39.000		35.085 34.990				
BB4016DP4						25.75								
BB4026DP4	40	44			53.50 52.50	16.25	39.975 39.950	44.025 44.000		40.085 39.990				
BB4516DP4						15.75								
BB4526DP4	45	50			2.505 2.460	2.60 2.30	58.50	44.975 44.950		50.025 50.000	45.105 44.990	0.155 0.015		
BB4526DP4							26.25 25.75							

8 Standard Products

8.3 DP4 Flanged Washers

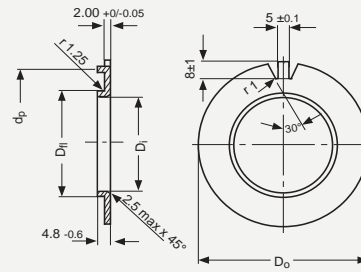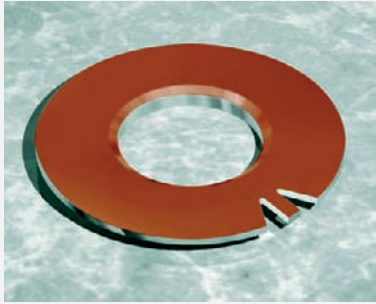



All dimensions in mm

Part No.	Inside- \varnothing D_i	Outside- \varnothing D_o	Flange- \varnothing D_{fl}	Location- \varnothing d_p
	max. min.	max. min.	max. min.	max. min.
BS40DP4	40.70 40.20	75.0 74.5	44.00 43.90	65.5 64.5
BS50DP4	51.50 51.00	85.0 84.5	55.00 54.88	75.5 74.5
BS60DP4	61.50 61.00	95.0 94.5	65.00 64.88	85.5 84.5
BS70DP4	71.50 71.00	110.0 109.5	75.00 74.88	100.5 99.5
BS80DP4	81.50 81.00	120.0 119.5	85.00 84.86	110.5 109.5
BS90DP4	91.50 91.00	130.0 129.5	95.00 94.86	120.5 119.5
BS100DP4	101.50 101.00	140.0 139.5	105.00 104.86	130.5 129.5

Corrosion Protection: Washers will be supplied covered with a light coating of oil.

Tab (Lug) Form: Washers are supplied with this feature in an unformed state (Flat). This feature may be supplied in the formed state only when requested by the customer.

8.4 DP4 Thrust Washers

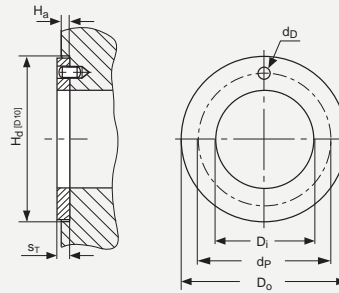
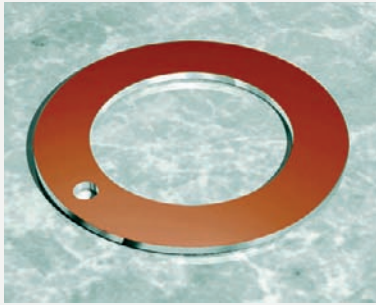


All dimensions in mm

Part No.	Inside- \varnothing D_i		Outside- \varnothing D_o	Thickness s_T	Dowel Hole		Recess Depth H_a
	min.	max.			$\varnothing d_D$	PCD- $\varnothing d_P$	
WC08DP4	10.00	10.25	20.00 19.75	1.50 1.45	No Hole	No Hole	1.20 0.95
WC10DP4	12.00	12.25	24.00 23.75		1.875 1.625	18.12 17.88	
WC12DP4	14.00	14.25	26.00 25.75		2.375 2.125	20.12 19.88	
WC14DP4	16.00	16.25	30.00 29.75			22.12 21.88	
WC16DP4	18.00	18.25	32.00 31.75		3.375 3.125	25.12 24.88	
WC18DP4	20.00	20.25	36.00 35.75			28.12 27.88	
WC20DP4	22.00	22.25	38.00 37.75		4.375 4.125	30.12 29.88	
WC22DP4	24.00	24.25	42.00 41.75			33.12 32.88	
WC24DP4	26.00	26.25	44.00 43.75		61.12 60.88	35.12 34.88	
WC25DP4	28.00	28.25	48.00 47.75			38.12 37.88	
WC30DP4	32.00	32.25	54.00 53.75		65.12 64.88	43.12 42.88	
WC35DP4	38.00	38.25	62.00 61.75			50.12 49.88	
WC40DP4	42.00	42.25	66.00 65.75		76.12 75.88	54.12 53.88	
WC45DP4	48.00	48.25	74.00 73.75			61.12 60.88	
WC50DP4	52.00	52.25	78.00 77.75	1.70 1.45	65.12 64.88		
WC60DP4	62.00	62.25	90.00 89.75		76.12 75.88		

8 Standard Products

8.5 DP4B Cylindrical bushes

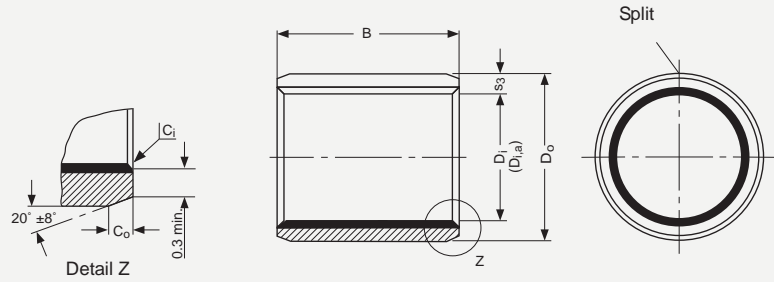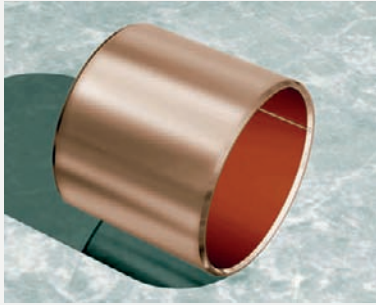

Dimensions and Tolerances according to ISO 3547 and GGB-Specifications

All dimensions in mm

Outside C_0 and Inside C_i chamfers

Wall thickness s_3	C_0 (a)		C_i (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s_3	C_0 (a)		C_i (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C_0 machined or rolled at the option of the manufacturer

b = C_i can be a radius or a chamfer in accordance with ISO 13715



Part No.	Nominal Diameter		Wall thickness s_3	Width B	Shaft- \varnothing D_J [h6, f7, h8]	Housing- \varnothing D_H [H6, H7]	Bush- \varnothing $D_{i,a}$ ass. in H6/H7 housing	Clearance C_D				
	D_i	D_o							max. min.	max. min.	max. min.	max. min.
0203DP4B	2	3.5	0.750 0.730	3.25	h6	H6	2.048 2.000	0.054 0.000				
0205DP4B				5.25					2.000	3.500		
0306DP4B	3	4.5		6.25					3.000	4.508	3.048	
0404DP4B				5.75					2.994	4.500	3.000	
0406DP4B	4	5.5		4.25					h7	H7	5.055 4.990	0.077 0.000
0505DP4B				3.75								
0510DP4B	5	7		6.25	4.990	7.015	5.055					
0606DP4B				5.75	4.978	7.000	4.990					
0608DP4B	6	8		8.25	f7	H7	8.055 7.990	0.083 0.003				
0610DP4B				7.75								
0808DP4B	8	10		10.25					5.978	8.000	5.990	
0810DP4B				9.75					7.987	10.015	8.055	
0812DP4B	8	10	12.25	f7					H7	10.058 9.990	0.086 0.003	
1010DP4B			11.75									7.972
1015DP4B	10	12	10.25		9.987	12.018	10.058					
1208DP4B			9.75		9.972	12.000	9.990					
1210DP4B	12	14	8.25		f7	H7	12.058 11.990	0.092 0.006				
1212DP4B			7.75									11.984
1215DP4B	12	14	10.25	11.966					14.000	11.990		
1215DP4B			9.75	11.966					14.000	11.990		

Part No.	Nominal Diameter		Wall thickness s ₃	Width B	Shaft-∅ D _J [h6, f7, h8]	Housing-∅ D _H [H6, H7]	Bush-∅ D _{i,a} ass. in H6/H7 housing	Clearance C _D												
	D _i	D _o							max. min.	max. min.	max. min.	max. min.	max. min.							
1410DP4B	14	16	1.005 0.980	10.25	f7	H7	13.984 13.966	16.018 16.000	0.092 0.006											
1415DP4B				9.75						15.25										
1420DP4B				14.75						20.25										
1515DP4B	15	17		15.25			14.984	17.018		15.058										
1525DP4B				14.75			14.966	17.000		14.990										
1615DP4B				25.25			15.984	18.018		16.058										
1625DP4B	16	18		24.75			15.966	18.000		15.990										
1820DP4B				20.25			1.505 1.475	f7		H7	20.021 20.000	18.061 17.990								
1825DP4B				19.75									17.984	20.000						
2015DP4B	24.75	17.966		20.000																
2020DP4B	20	23		20.25							1.505 1.475	f7	H7	23.021 23.000	20.071 19.990					
2025DP4B				19.75												19.980	23.000			
2030DP4B			25.25	19.959	23.000															
2215DP4B	22	25	24.75	30.25	1.505 1.475	f7			H7					25.021 25.000	22.071 21.990					
2220DP4B			29.75	15.25												21.980	25.000			
2225DP4B			14.75	14.75												21.959	25.000			
2515DP4B	25	28	20.25	20.25										1.505 1.475	f7	H7	28.021 28.000	25.071 24.990		
2525DP4B			19.75	24.75															24.980	28.000
2830DP4B			24.75	27.980															32.025	28.085
3020DP4B	30	34	29.75	27.959			2.005 1.970	f7		H7							32.000	28.085 27.990		
3030DP4B			20.25	29.980															34.025	30.085
3040DP4B			19.75	29.959															34.000	29.990
3520DP4B	35	39	40.25	2.005 1.970							f7	H7	39.025 39.000				35.085 34.990			
3530DP4B			39.75															34.975	39.000	
4030DP4B			29.75															34.950	39.000	
4050DP4B	40	44	39.75		39.975	2.005 1.970			f7				H7				44.025 44.000	40.085 39.990		
4530DP4B			50.25		44.975														50.025	45.105
4550DP4B			49.75		44.950														50.000	44.990
5040DP4B	50	55	30.25		49.975									2.505 2.460	f7	H7	55.030 55.000	50.110 49.990		
5060DP4B			29.75		49.950														55.000	
5540DP4B			60.25		54.970														60.030	55.110
6040DP4B	60	65	59.75		54.940		2.505 2.460	f7		H7							60.000	54.990		
6050DP4B			40.25		59.970														65.030	60.110
6060DP4B			49.75		59.940														65.000	59.990
6070DP4B	60	65	60.25	2.505 2.460	f7						H7	70.030 70.000					65.110 64.990			
6570DP4B			69.75															64.970	70.000	
6570DP4B	65	70	69.75									64.940					70.000	64.990		

8 Standard Products

Part No.	Nominal Diameter		Wall thickness s_3		Width B	Shaft- \varnothing D_J [h6, f7, h8]		Housing- \varnothing D_H [H6, H7]		Bush- \varnothing $D_{i,a}$ ass. in H6/H7 housing		Clearance C_D
	D_i	D_o	max. min.	max. min.		max. min.	max. min.	max. min.	max. min.	max. min.		
7050DP4B	70	75	2.505 2.460	50.25	f7	69.970 69.940	75.030 75.000	70.110 69.990	0.170 0.020			
7070DP4B				70.25 69.75								
7580DP4B	75	80	2.505 2.460	80.25	f7	74.970 74.940	80.030 80.000	75.110 74.990	0.170 0.020			
7580DP4B				79.75								
8060DP4B	80	85	2.490 2.440	60.50	h8	80.000 79.946	85.035 85.000	80.155 80.020	0.201 0.020			
80100DP4B				59.50								
85100DP4B	85	90	2.490 2.440	100.50	h8	85.000 84.946	90.035 90.000	85.155 85.020	0.209 0.020			
85100DP4B				99.50								
9060DP4B	90	95	2.490 2.440	60.50	h8	90.000 89.946	95.035 95.000	90.155 90.020	0.209 0.020			
90100DP4B				59.50								
95100DP4B	95	100	2.490 2.440	100.50	h8	95.000 94.946	100.035 100.000	95.155 95.020	0.209 0.020			
95100DP4B				99.50								
10060DP4B	100	105	2.490 2.440	60.50	h8	100.000 99.946	105.035 105.000	100.155 100.020	0.209 0.020			
100115DP4B				59.50								
105115DP4B	105	110	2.490 2.440	115.50	h8	105.000 104.946	110.035 110.000	105.155 105.020	0.209 0.020			
105115DP4B				114.50								
110115DP4B	110	115	2.490 2.440	115.50	h8	110.000 109.946	115.035 115.000	115.155 115.020	0.209 0.020			
110115DP4B				114.50								

8.6 DP4B Flanged bushes

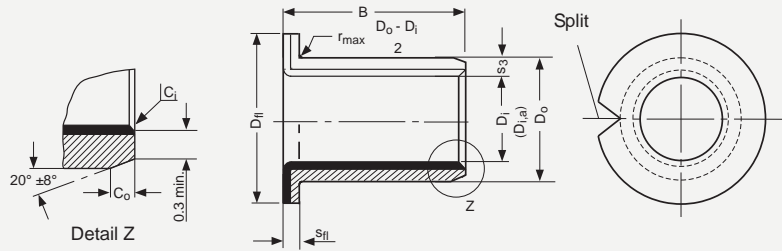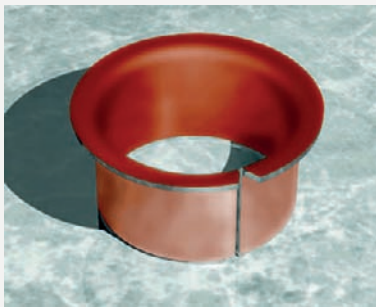

Dimensions and Tolerances according to ISO 3547 and GGB-Specifications

All dimensions in mm

Outside C_o and Inside C_i chamfers

Wall thickness s_3	C_o (a)		C_i (b)
	machined	rolled	
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7

Wall thickness s_3	C_o (a)		C_i (b)
	machined	rolled	
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

a = Chamfer C_o machined or rolled at the option of the manufacturer




b = C_i can be a radius or a chamfer in accordance with ISO 13715

Part No.	Nominal Diameter		Wall thickness s_3	Flange thickness s_{fl}	Flange- \varnothing D_{fl}	Width B	Shaft- \varnothing D_J [h6, f7, h8]		Housing- \varnothing D_H [H6, H7]		Bush- \varnothing $D_{i,a}$ Ass. in H6/H7 housing	Clearance C_D
	D_i	D_o					max. min.	max. min.	max. min.	max. min.		
BB0304DP4B	3	4.5	0.750 0.730	0.80 0.70	7.50	4.25	h6	3.000	H6	4.508	3.048	0.054
BB0404DP4B					6.50			2.994		4.500		
BB0404DP4B	4	5.5	0.750 0.730	0.80 0.70	9.50	3.75	h6	4.000	H6	5.508	4.048	0.056
BB0404DP4B					8.50			3.992		4.500		
BB0505DP4B	5	7	1.005 0.980	1.05 0.80	10.50	5.25	f7	4.990	H7	7.015	5.055	0.077
BB0505DP4B					9.50			4.978		7.000		

Part No.	Nominal Diameter		Wall thickness s ₃	Flange thickness s _{fl}	Flange-∅ D _{fl}	Width B	Shaft-∅ D _j [h6, f7, h8]	Housing-∅ D _H [H6, H7]	Bush-∅ D _{i,a} Ass. in H6/H7 housing	Clearance C _D					
	D _i	D _o	max min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.	max. min.					
BB0604DP4B	6	8	1.005 0.980	1.05 0.80	12.50	4.25 3.75	f7	H7	6.055 5.990	0.077 0.000					
BB0608DP4B					11.50	8.25 7.75					5.990 5.978	8.015 8.000			
BB0806DP4B	8	10			15.50	5.75 5.25					7.987	10.015	8.055	0.083	
BB0810DP4B					14.50	9.75 9.25					7.972	10.000	7.990	0.000	
BB1007DP4B	10	12			18.50	7.25 6.75					9.987	12.018	10.058	0.086	
BB1012DP4B					17.50	12.25 11.75					9.972	12.000	9.990	0.003	
BB1207DP4B	12	14			20.50	7.25 6.75					11.984 11.966	14.018 14.000	12.058 11.990	0.092 0.006	
BB1209DP4B					19.50	9.25 8.75									
BB1212DP4B					12.25 11.75										
BB1417DP4B	14	16			22.50 21.50	12.25 11.75					13.984 13.966	16.018 16.000	14.05 13.990		
BB1512DP4B	15	17			23.50	12.25 11.75					14.984	17.018	15.058		0.006
BB1517DP4B					22.50	17.25 16.75					14.966	17.000	14.990		
BB1612DP4B	16	18			24.50	12.25 11.75					15.984 15.966	18.018 18.000	16.058 15.990		
BB1617DP4B					23.50	17.25 16.75									
BB1812DP4B	18	20			26.50	12.25 11.75					17.984 17.966	20.021 20.000	18.061 17.990		0.095 0.006
BB1822DP4B					25.50	22.25 21.75									
BB2012DP4B	20	23	30.50	11.75 11.25	19.980 19.959	23.021 23.000	20.071 19.990	0.112 0.010							
BB2017DP4B			29.50	16.75 16.25											
BB2512DP4B	25	28	35.50	11.75 11.25	24.980 24.959	28.021 28.000	25.071 24.990								
BB2522DP4B			34.50	21.75 21.25											
BB3016DP4B	30	34	42.50	16.25 15.75	29.980 29.959	34.025 34.000	30.085 29.990		0.126 0.010						
BB3026DP4B			41.50	26.25 25.75											
BB3526DP4B	35	39	47.50 46.50	26.25 25.75	34.975 34.950	39.025 39.000	35.085 34.990		0.135 0.015						
BB4026DP4B	40	44	53.50 52.50	26.25 25.75	39.975 39.950	44.025 44.000	40.085 39.990		0.135 0.015						
BB4526DP4B	45	50	58.50 57.50	26.25 25.75	44.975 44.950	50.025 50.000	45.105 44.990	0.155 0.015							

8 Standard Products




8.7 DP4 Strip

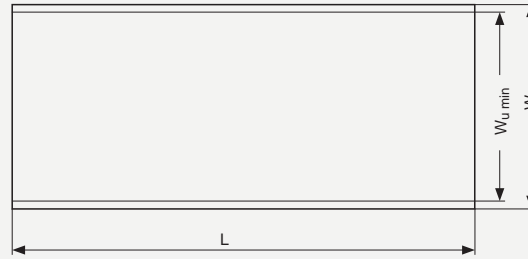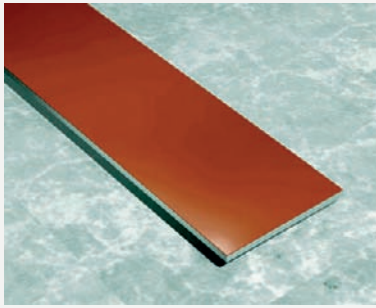

All dimensions in mm

Part No.	Length L		Total Width W	Usable Width $W_{U \min}$	Thickness s_S	
	max.	min.			max.	min.
S07190DP4	503	500	200	190	0.74	0.70
S10190DP4					1.01	0.97
S15190DP4					1.52	1.48
S20190DP4					1.98	1.94
S25240DP4			2.46	2.42	254	240

8.8 DP4B Strip

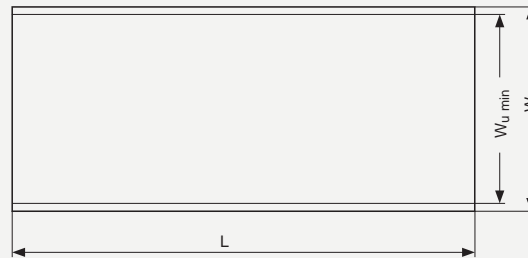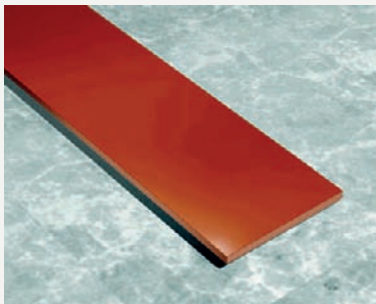

All dimensions in mm

Part No.	Length L		Total Width W	Usable Width $W_{U \min}$	Thickness s_S	
	max.	min.			max.	min.
S07085DP4B	503	500	95	85	0.74	0.70
S10180DP4B			195	180	1.01	0.97
S15180DP4B					1.52	1.48
S20180DP4B					1.98	1.94
S25180DP4B			2.46	2.42		

9 Test Methods

9.1 Measurement of Wrapped Bushes

It is not possible to accurately measure the external and internal diameters of a wrapped bush in the free condition. In its free state a wrapped bush will not be perfectly cylindrical and the butt joint may be open. When correctly installed in a housing the butt joint will be tightly closed and the bush will

conform to the housing. For this reason the external diameter and internal diameter of a wrapped bush can only be checked with special gauges and test equipment.

The checking methods are defined in ISO 3547 Part 1 to 7.

Test A of ISO 3547 Part 2

Checking the external diameter in a test machine with checking blocks and adjusting mandrel.

Test A of ISO 3547 Part 2 on 2015DP4	
Checking block and setting mandrel $d_{ch,1}$	23.062 mm
Test force F_{ch}	4500 N
Limits for Δz	0 and -0.065 mm
Bush Outside diameter D_o	23.035 to 23.075 mm

Table 18: Test A of ISO 3547 Part 2

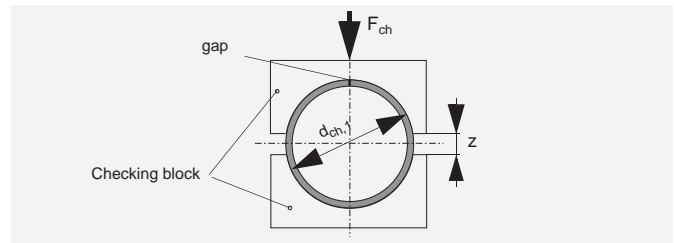


Fig. 40: Test A, Data for drawing

Test B (alternatively to Test A)

Check external diameter with GO and NO GO ring gauges.

Test C

Checking the internal diameter of a bush pressed into a ring gauge, which nominal diameter corresponds to the dimension specified in table 6 of ISO 3547 Part 1.

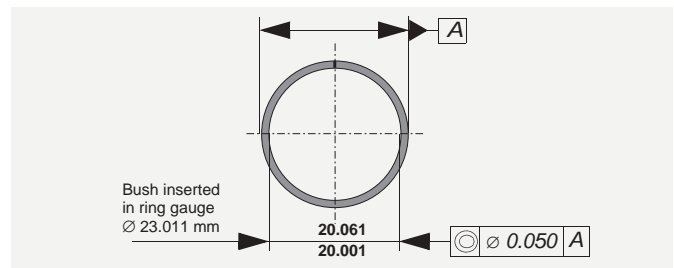


Fig. 41: Test C, Data for drawing (example $D_i = 20$ mm)

Measurement of Wall Thickness (alternatively to Test C)

The wall thickness is measured at one, two or three positions axially according to the bearing dimensions.

B [mm]	X [mm]	Measurement position
≤ 15	B/2	1
$>15 \leq 50$	4	2
$>50 \leq 90$	6 and B/2	3
>90	8 and B/2	3

Table 19: Measurement position for wall thickness

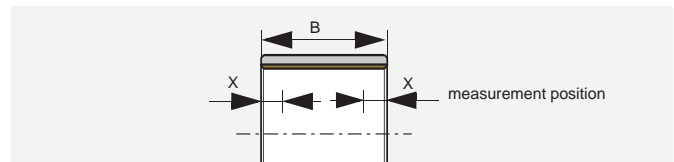


Fig. 42: Wall thickness measurement position

Test D

Check external diameter by precision measuring tape.

10 Data Sheet for bearing design

Company:

Project:

Application:

Date:

Existing Design New Design
 Quantity Annual


Contact name:

Tel.:

Fax:

Email:

Drawing attached YES NO

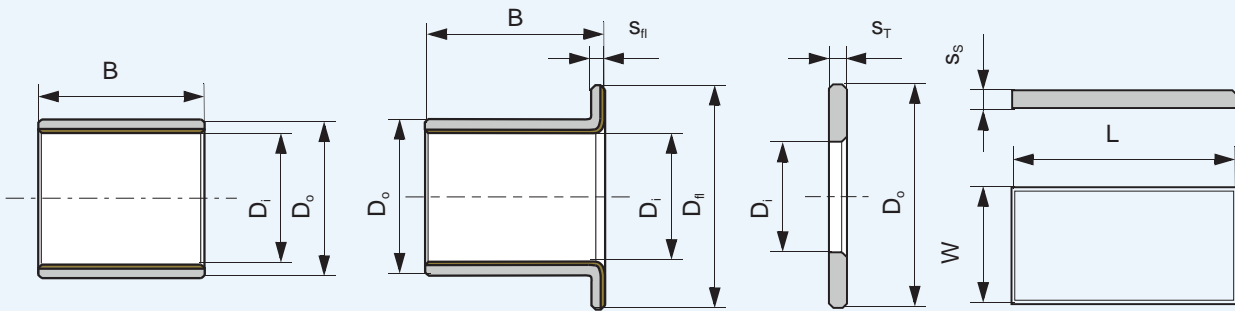

Cylindrical Bush Flanged Bush Thrust Washer Slideplate Special (Sketch)

Steady load Rotating load Rotational movement Oscillating movement Linear movement

Dimensions in mm

Inside Diameter D_i
 Outside Diameter D_o
 Length B
 Flange Diameter D_{fl}
 Flange Thickness s_{fl}
 Length of slideplate L
 Width of slideplate W
 Thickness of slideplate s_s

Load

Radial load F [N]
 Axial load F [N]

Movement

Rotational speed n [1/min]
 Speed v [m/s]
 Length of Stroke L_s [mm]
 Frequency of Stroke [1/min]
 Angular displacement φ [°]
 Oscillating frequency n_{osc} [1/min]

Service hours per day

Continuous operation [h]
 Intermittent operation [h]

Fits and Tolerances

Housing (\varnothing , tolerance) D_H
 Shaft (\varnothing , tolerance) D_J

Mating surface

Material
 Hardness HB/HRC
 Surface roughness R_a [μm]

Operating Environment

Temperature - ambient T_{amb}
 Temperature - min/max T_{min}/T_{max}

Housing material

Assembly with good heat transfer properties

Assembly with poor heat transfer properties

Dry operation With lubricant

If grease, type with technical datasheet
 If oil, type with technical datasheet

- Oil splash
 - Oil bath
 - Oil circulation

Service life

Required service life L_H [h]

Formula Symbols and Designations

Formula Symbol	Unit	Designation
A	mm ²	Surface area of DP4 bearing
A _M	mm ²	Surface area of mating surface in contact with DP4 bearing (slideway)
a _B	-	Bearing size factor
a _C	-	Application factor for bore burnishing
a _E	-	High load factor
a _{E1}	-	Specific load factor (slideways)
a _{E2}	-	Speed, temperature and material factor (slideways)
a _{E3}	-	Relative contact area factor (slideways)
a _L	-	Life correction constant
a _M	-	Mating surface material factor
a _T	-	Temperature application factor
B	mm	Nominal bush width
C	1/min	Dynamic load frequency
C _D	mm	Installed diametral clearance
C _i	mm	Inside chamfer
C _o	mm	Outside chamfer
C _T	-	Total number of dynamic load cycles
D _C	mm	Diameter of burnishing tool
D _{fl}	mm	Nominal bush flange OD
D _H	mm	Housing diameter
D _i	mm	Nominal bush and thrust washer ID
D _{i,a}	mm	Bush ID when assembled in housing
D _J	mm	Shaft diameter
D _{Nth}	nvt	Max. thermal neutron dose
D _o	mm	Nominal bush and thrust washer OD
D _γ	Gy	Max. Gamma radiation dose G _γ = J/kg
d _D	mm	Dowel hole diameter
d _L	mm	Oil hole diameter
d _P	mm	Pitch circle diameter for dowel hole
F	N	Bearing load
F _{ch}	N	Test load
F _i	N	Insertion force
f	-	Coefficient of friction

Formula Symbol	Unit	Designation
H _a	mm	Depth of housing recess (e.g. for thrust washers)
H _d	mm	Diameter of housing recess (thrust washers)
L	mm	Strip length
L _H	h	Bearing service life
L _S	mm	Length of stroke (slideway)
n	1/min	Rotational speed
n _E	1/min	Equivalent rotational speed for oscillating movement
n _{osc}	1/min	Oscillating movement frequency
p	MPa	Specific load
p _{lim}	MPa	Specific load limit
p _{sta,max}	MPa	Maximum static load
p _{dyn,max}	MPa	Maximum dynamic load
Q	-	Number of load/movement cycles
R _a	μm	Surface roughness (DIN 4768, ISO/DIN 4287/1)
R _{OB}	Ω	Electrical resistance
s ₃	mm	Bush wall thickness
s _{fl}	mm	Flange thickness
s _S	mm	Strip thickness
s _T	mm	Thrust washer thickness
T	°C	Temperature
T _{amb}	°C	Ambient temperature
T _{max}	°C	Maximum temperature
T _{min}	°C	Minimum temperature
v	m/s	Sliding speed
W	mm	Strip width
W _{u min}	mm	Minimum usable strip width
Z _T	-	Total number of cycles
α ₁	10 ⁻⁶ /K	Coefficient of linear thermal expansion parallel to surface
α ₂	10 ⁻⁶ /K	Coefficient of linear thermal expansion normal to surface
σ _c	MPa	Compressive yield strength
λ	W/mK	Thermal conductivity
φ	°	Angular displacement
η	cP	Dynamic viscosity

10 Data Sheet for bearing design







Product Information

GGB gives an assurance that the products described in this document have no manufacturing errors or material deficiencies.

The details set out in this document are registered to assist in assessing the material's suitability for the intended use. They have been developed from our own investigations as well as from generally accessible publications. They do not represent any assurance for the properties themselves.

Unless expressly declared in writing, GGB gives no warranty that the products described are suited to any particular purpose or specific operating circumstances. GGB accepts no liability for any losses, damages or costs however they may arise through direct or indirect use of these products.

GGB's sales and delivery terms and conditions, included as an integral part of quotations, stock and price lists, apply absolutely to all business conducted by GGB. Copies can be made available on request.

Products are subject to continual development. GGB retains the right to make specification amendments or improvements to the technical data without prior announcement.

Edition 2009 (This edition replaces earlier editions which hereby lose their validity).

Declaration on lead contents of GGB products/compliance with EU law

Since July 1, 2006 it has been prohibited under Directive 2002/95/EC (restriction of the use of certain hazardous substances in electrical and electronic equipment; ROHS Directive) to put products on the market that contain lead, mercury, cadmium, hexavalent chromium, polybrominated biphenyls (PBB) or polybrominated diphenyl ethers (PBDE).

Certain applications listed in the annex to the ROHS Directive are exempted. A maximum concentration value of 0.01% by weight and per homogeneous material, for cadmium and of 0.1% by weight and per homogeneous material, for lead, mercury, hexavalent chromium, PBB and PBDE shall be tolerated.

According to Directive 2000/53/EC on end-of life vehicles, since July 1, 2003 it has been prohibited to put on the market materials and components that contain lead, mercury, cadmium or hexavalent chromium. Due to an exceptional provision, lead-containing bearing shells and bushes could still be put on the market up until July 1, 2008. This general exception expired on July 1, 2008. A maximum concentration value of up to 0.1% by weight and per homogeneous material, for lead, hexavalent chromium and mercury shall be tolerated.

All products of GGB, with the exception of DU, DUB, DB, SY and SP satisfy these requirements of Directives 2002/95/EC (ROHS Directive) and 2000/53/EC (End-of-life Vehicle Directive).

All products manufactured by GGB are also compliant with REACH Regulation (EC) No. 1 907/2006 of December 18, 2006.

Health Hazard - Warning

Fabrication

At temperatures up to 250 °C the polytetrafluoroethylene (PTFE) present in the lining material is completely inert so that even on the rare occasions in which DP4 bushes are drilled, or sized, after assembly there is no danger in boring or burnishing.

At higher temperatures however, small quantities of toxic fumes can be produced and the direct inhalation of these can cause an influenza type of illness which may not appear for some hours but which subsides without after-effects in 24-48 hours.

Such fumes can arise from PTFE particles picked up on the end of a cigarette. Therefore smoking should be prohibited where DP4 is being machined.

DP4®, DP4-B™, DX®, DX®10, DS™ and HI-EX® are trademarks of GGB.

Visit us on the internet:
www.ggbearings.com





an EnPro Industries company

The Global Leader in High Performance Bearing Solutions

GGB North America

700 Mid Atlantic Parkway

Thorofare, New Jersey, 08086 USA

Tel. +1-856-848-3200 • Fax +1-856-848-5115

email: usa@ggbearings.com • www.ggbearings.com



HB104ENG12-15USA